



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS

मानक भवन, 9 बहादुरशाह जफर मार्ग, नई दिल्ली 110002
Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

टेलीफोन] 3230131 टेलीग्राम] फैक्स] +91 11 3234062 तार : मानकसंस्था
Phones] 3238375 Telex] 031-65870 Fax] +91 11 3239399 Grams : Manaksanstha
3239402

Our Ref: CED 53:2/T-1

1997-12-26

Subject: Inclusion of pipes using vibration
process in IS 458

Patel Hume Pipe Factory
Patel Compound
Bodeli 391 135
Dist. Vadodara, Gujarat

Dear Sir,

This has reference to your letter dated 1 September 1997 regarding inclusion of requirements of concrete pipes manufacturing by casting in IS 458:1988. The above proposal was considered by the concerned Concrete Pipes Subcommittee, CED 53:2. The Committee had in principle agreed to the above proposal. However the Committee desired that the convener of CED 53 should review the details submitted by you. The views received from the Convener alongwith the tables giving various requirements for different classes of pipes are now being circulated to members for their comments. As per our procedure, the comments received, if any, on the above proposal will be discussed in the next meeting and will be further processed accordingly. A copy of the proposal is enclosed for your reference.

Thanking you,

Yours faithfully,

(J.K. Prasad)

Addl Director (Civil Engg.)

32

AMENDMENT NO. 4 MARCH 2003
TO
IS 458 : 1988 SPECIFICATION FOR PRECAST
CONCRETE PIPES (WITH AND WITHOUT
REINFORCEMENT)
(Third Revision)

[Page 21, clause 9.2.1 (see Amendment No. 3)] — Substitute the following for the existing:

'9.2.1 Permeability test when conducted in accordance with the method described in IS 3597 shall meet requirement of final permeability, which shall not exceed 0.3 cm^3 .

NOTE — It is recommended that initial absorption should not exceed 2.0 cm^3 and the difference in any two readings during initial absorption should not be more than 0.8 cm^3 .

[Page 21, Fig. 5 (see Amendment No. 3)] — Delete.

[Page 21, clause 9.2.1.1 (see Amendment No. 3)] — Delete.

[Page 21, clause 9.2.1.2 (see Amendment No. 3)] — Delete.

[Page 3, clause 4.7 (see Amendment No. 3)] — Substitute the following for the existing:

'4.7 Water — Water used for mixing of concrete and curing of pipes shall conform to 5.4 of IS 456 : 2000.'

(CED 53)

AMENDMENT NO. 3 SEPTEMBER 2001
TO
IS 458:1988 SPECIFICATION FOR PRECAST CONCRETE PIPES
(WITH AND WITHOUT REINFORCEMENT)

(Third Revision)

- (Page 2, clause 0.3.1) — Insert the following at the end :
'The inclusion of details of NP3 and NP4 classes of pipes to be manufactured by casting process.'
- (Page 2, clause 0.3.2) — Delete.
- (Page 2, clause 0.3.3) (see also Amendment No. 1) — Delete.
- (Page 2, clause 3.1, informal table, col 2, against Class NP3 and NP4) — Insert 'and also unreinforced (i.e. case of pipes manufactured by casting process)' after the word 'reinforced'.
- (Page 3, clause 4.2) — Insert 'or IS 12269:1987¹⁴' at the end.
- (Page 3, clause 4.4, first sentence) — Substitute the following for the existing sentence :
'Reinforcement used for the manufacture of reinforced concrete pipes shall conform to mild steel grade I or medium tensile steel bars of IS 432 (Part 1) : 1982⁸ or hard-drawn steel wire of IS 432 (Part 2) : 1982⁹ or structural steel (standard quality) bars of IS 2062:1992¹⁰.'
- (Page 3, clause 4.4, Note) — Substitute the following for the existing Note:
NOTE — Wire fabric conforming to IS 1566:1982¹¹ or deformed bars and wires conforming to IS 1786 : 1985¹² or plain hard-drawn steel wire for prestressed concrete conforming to IS 1785 (Part 1) : 1983¹³ or IS 1785 (Part 2) : 1983¹⁴ may also be used. For such reinforcement maximum tensile stress shall be as given in 5.1.'
- (Page 3, clause 4.5, first sentence) — Delete.
- (Page 3, footnote 10) — Substitute the following for the existing footnote:
'Specification for steel for general structural purposes (fourth revision).'
- (Page 3, footnote 14) — Delete footnote 14 and insert the following new footnotes :
'Specification for 53 grade ordinary Portland cement
'Specification for plain hard-drawn steel wire for prestressed concrete (Part 1) Cold-drawn stress relieved wire (second revision)
'Specification for plain hard-drawn steel wire for prestressed concrete (Part 2) As drawn wire (first revision).'
- (Page 3, clause 4.5.1, para 1) — Insert the following at the end of the para:
'However in case of pipes manufactured by casting process, concrete shall have minimum compressive strength as indicated in the Tables 3A, 3B, 4A and 4B for the respective classes of pipe.'
- (Page 3, clause 4.6) — Insert the following new clauses after 4.6:
4.7 Water — Water used for mixing of concrete and curing of pipes shall conform to 4.3 of IS 456 : 2000⁵
4.8 Chemical Admixtures — The admixtures, where used, shall conform to IS 9103 : 1999⁶
- (Page 3, clause 5.1.1) — Substitute the following for the existing clause:
5.1.1 The barrel wall thickness shall be such that under the specified hydrostatic test pressure, the maximum tensile stress in concrete, when considered as effective to take stress along with the tensile reinforcement, shall not exceed 2 N/mm² for pressure pipes and 1.5 N/mm² for non-pressure pipes. But the wall thickness shall be not less than those given in Tables 1 to 7 subject to 7.2(c), in case of pipes manufactured by spinning process. For pipes manufactured by casting process, the wall thickness shall be as given in Tables 3A, 3B, 4A and 4B.'
- (Page 3, footnotes below clause 5.1.1) — Substitute the following footnote 2 for the existing footnote 2 and insert the following new footnote 5:
Code of practice for plain and reinforced concrete (fourth revision)
'Specification for admixtures for concrete', (second revision)
- (Page 4, clause 5.1.3) — Insert the following at the end of the clause
in case of pipes manufactured by spinning process. For reinforced pipes manufactured by casting process, the minimum longitudinal reinforcement shall be as given in Tables 3B and 4B.'

Amendment No. 3 to IS 458 : 1988

[Page 4, clause 5.2.2, last sentence (see also Amendment No. 2)] — Substitute the following for the existing last sentence:

'In the absence of calculations and tests, the reinforcement given in Tables 2 to 7 for pipes manufactured with spinning method and in Tables 3B and 4B for pipes manufactured by casting process shall be used as minimum reinforcement subject to the requirements of 5.2.2.1.'

[Page 4, clause 5.3, (see also Amendment No. 2)] — Substitute the following for existing clause:

'5.3 The ends of concrete pipes used for water mains, sewers and irrigation shall be suitable for socket and spigot, roll on joints or confined gasket joints. Dimensions of spigot and socket for rubber ring roll on jointed pipes shall be as given in Tables 8 to 13 for pipes manufactured by spinning process. However, the dimensions of spigot and socket shall be as given in Tables 10A and 10B in case of pipes manufactured by casting process. Reinforcement in socket of rubber ring jointed pipes shall be as given in Table 14. However the ends of concrete pipes used for road culverts may be suitable for flush or collar joints (see Fig. 1 and Fig. 2). Dimensions of collars shall be according to details given in Tables 1, 15 and 16. The reinforcement for collars shall be as given in Tables 15 and 16. The ends of collar reinforcement shall have a full ring at both ends.'

(Page 4, clause 5.3, Note 2) — Delete Note 2 and renumber Note 3 as Note 2.

(Page 4, clause 5.3.1) — Insert the following in the beginning:

'Only flexible rubber ring joints shall be used in the joints in (a) all pressure pipes, and (b) all non-pressure pipes except when used for road culverts.'

(Page 8, Table 3, col 1, heading) — Delete the word 'Nominal'.

(Page 8, Table 3, Note 1) — Delete.

(Page 8, Table 3) — Insert the following new Tables after Table 3:

Table 3A Design and Strength Test Requirements of Concrete Pipes of Class NP3 — Unreinforced Concrete, Medium-Duty, Non-Pressure Pipes Made by Casting Process
(Clauses 4.5.1, 5.1.1, 5.3 and 7.1)

Internal Diameter of Pipes	Barrel Wall Thickness	Strength Test Requirement for Three Edge Bearing Test, Ultimate Load
mm (1)	mm (2)	kN/linear metre (3)
300	50	15.50
350	55	16.77
400	60	19.16
450	65	21.56
500	70	23.95
600	75	28.74
700	85	33.53
800	95	38.32
900	100	43.11
1 000	115	47.90
1 100	120	52.69
1 200	125	57.48
1 400	140	67.06
1 600	165	76.64
1 800	180	86.22

NOTE — Concrete for pipes shall have a minimum compressive strength of 45 N/mm² at 28 days.

Table 3B Design and Strength Test Requirements of Concrete Pipes of Class NP3 — Reinforced Concrete, Medium-Duty, Non-Pressure Pipes Made by Casting Process

(Clauses 5.1.1, 5.1.2, 5.1.3, 6.3.2 and 7.1)

Internal Diameter of Pipes	Barrel Wall Thickness	Reinforcements			Strength Test Requirements for Three Edge Bearing Test	
		Longitudinal, Mild Steel or Hard-Drawn Steel		Spiral Hard-Drawn Steel kg/linear metre	Load to Produce 0.25 mm Crack kN/linear metre	Ultimate Load kN/linear metre
		Min number	kg/linear metre			
mm	mm	(3)	(4)	(5)	(6)	(7)
300	50	8	0.78	1.53	15.50	23.25
350	55	8	0.78	1.58	16.77	25.16
400	60	8	0.78	1.60	19.16	28.74
450	65	8	0.78	1.90	21.56	32.34
500	70	8	0.78	2.00	23.95	35.93
600	75	8 or 6+6	1.18	2.20	28.74	43.11
700	85	8 or 6+6	1.18	4.87	33.53	50.30
800	95	8 or 6+6	2.66	6.87	38.32	57.48
900	100	6+6	2.66	11.55	43.11	64.67
1 000	115	6+6	2.66	15.70	47.90	71.85
1 100	120	6+6	2.66	19.61	52.69	79.00
1 200	125	8+8	3.55	21.25	57.48	86.22
1 400	140	8+8	3.55	30.00	67.06	100.60
1 600	165	8+8	3.55	50.63	76.64	114.96
1 800	180	12+12	9.36	64.19	86.22	129.33
2 000	190	12+12	9.36	83.12	95.80	143.70
2 200	210	12+12	9.36	105.53	105.40	158.07
2 400	225	12+12	14.88	133.30	115.00	172.44

NOTE — Concrete for pipes shall have a minimum compressive strength of 35 N/mm² at 28 days

[Page 9, Table 4, col 1, heading (see also Amendment No. 2)]: Delete the word 'Nominal'.

(Page 9, Table 4, Note 1) — Delete

(Page 9, Table 4) — Insert the following new Tables 4A and 4B after Table 4:

Table 4A Design and Strength Test Requirements of Concrete Pipes of Class NP4 — Unreinforced Concrete, Heavy-Duty, Non-Pressure Pipes Made by Casting Process

(Clauses 5.1.1, 5.3 and 7.1)

Internal Diameter of Pipes	Barrel Wall Thickness	Strength Test Requirements for Three Edge Bearing Test, Ultimate Load
mm	mm	kN/linear metre
(1)	(2)	(3)
300	50	26.4
350	55	29.8
400	60	33.9
450	65	36.9
500	70	40.0
600	75	46.3
700	85	52.2
800	95	59.3
900	100	66.3
1 000	115	72.6
1 100	125	81.4
1 200	135	87.4
1 400	155	102.2
1 600	180	119.6
1 800	210	135.3

NOTE — Concrete for pipes shall have a minimum compressive strength of 27 N/mm² at 28 days

Table 4B Design and Strength Test Requirements of Concrete Pipes of Class NP4 — Reinforced Concrete, Heavy-Duty, Non-Pressure Pipes Made by Casting Process
(Clauses 5.1.1, 5.1.2, 5.1.3, 6.3.2 and 7.1)

Internal Diameter of Pipes	Barrel Wall Thickness	Reinforcements			Strength Test Requirements for Three Edge Bearing Test	
		Longitudinal Mild Steel or Hard-Drawn Steel		Spiral Hard-Drawn Steel	Load to Produce 0.25 mm Crack kN/linear metre	Ultimate Load kN/linear metre
		A _{lin} number	kg/linear metre			
mm	mm	(3)	(4)	(5)	(6)	(7)
(1)	(2)	(3)	(4)	(5)	(6)	(7)
300	50	8	0.78	1.53	26.4	39.6
350	55	8	0.78	1.61	29.8	44.7
400	60	8	0.78	1.97	33.9	50.9
450	65	8	0.78	3.36	36.9	55.3
500	70	8	0.78	5.56	40.0	61.2
600	75	8 or 6+6	2.34	8.50	46.3	69.4
700	85	8 or 6+6	3.44	12.78	52.2	78.3
800	95	8 or 6+6	3.44	16.72	59.3	87.1
900	100	6+6	3.44	20.92	66.3	99.4
1 000	115	8+8	6.04	26.70	72.6	108.9
1 100	120	8+8	6.04	35.60	80.4	120.6
1 200	125	8+8	6.04	42.42	88.3	132.4
1 400	140	8+8	9.36	53.39	104.2	156.4
1 600	165	12+12	9.36	79.92	119.6	179.5
1 800	180	12+12	14.88	85.75	135.3	203.0

NOTE — Concrete for pipes shall have a minimum compressive strength of 35 N/mm² at 28 days

(Page 12, Table 8) — Insert the following Note at the end of the Table :

NOTE — The dimensions D, h and e shall conform to the values given in this table as these are critical dimensions. The tolerances for dimensions shall apply on the critical dimensions.


Dimension	Tolerances
D	± 3 mm for pipes up to and including 300 mm internal diameter ± 4 mm for pipes over 300 mm internal diameter
h	± 3 mm for dimensions up to 60 mm ± 5 mm for dimensions above 60 mm
e	± 2 mm for dimensions up to 30 mm ± 3 mm for dimensions above 30 mm

(Page 14, Table 10) — Insert the following new Tables 10A and 10B after Table 10:

Table 10A Spigot and Socket Dimensions for NP3 Reinforced and Unreinforced and NP4 Reinforced Pipes Made by Vertical Casting Process

(Clause 5.3)

All dimensions in millimetres.

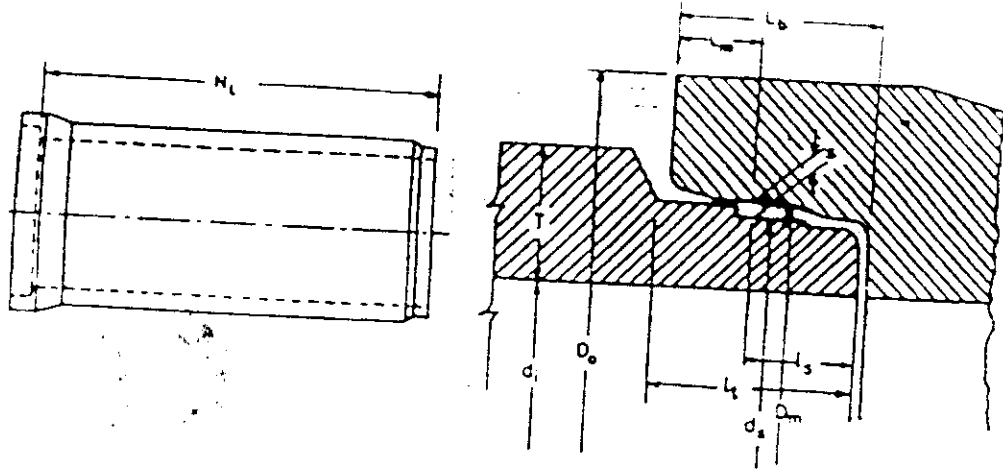

d_1	G	R	T	D_o	l_1	L_2	d_1	D_m	L_m	l_1	S
300±4	13	322	50	487±4	112±4	105±2	370.07	386.07	49	50	8.00±1.0
350±5	13	370	55	555±4	112±4	105±2	425.07	441.07	49	50	8.00±1.0
400±5	13	417	60	615±4	112±4	105±2	480.07	496.07	49	50	8.00±1.0
450±5	13	465	65	680±4	112±4	105±2	536.07	552.07	49	50	8.00±1.0
500±5	13	513	70	735±4	112±4	105±2	590.07	606.07	49	50	8.00±1.0
600±5	13	609	75	850±4	112±4	105±2	700.07	716.07	49	50	8.00±1.0
700±7	18	706	85	980±5	141±5	132±3	808.00	830.00	61	65	11.00±1.2
800±7	18	803	95	1 100±5	141±5	132±3	924.00	946.00	61	65	11.00±1.2
900±7	18	901	100	1 215±5	141±5	132±3	1 036.00	1 058.00	61	65	11.00±1.2
1 000±7	18	998	115	1 330±5	141±5	132±3	1 148.00	1 170.00	61	65	11.00±1.2
1 100±7	24	1 097	120	1 520±6	155±6	145±3	1 262.00	1 291.30	72	63	14.65±1.5
1 200±7	24	1 195	125	1 640±6	155±6	145±3	1 372.48	1 401.78	72	63	14.65±1.5
1 400±10	24	1 383	140	1 870±6	155±6	145±3	1 590.91	1 620.21	72	63	14.65±1.5
1 600±10	24	1 578	165	2 100±6	155±6	145±3	1 814.91	1 844.21	72	63	14.65±1.5
1 800±10	24	1 774	180	2 340±6	155±6	145±3	2 040.00	2 069.30	72	63	14.65±1.5

G = diameter of the unstretched rubber chord, hardness 40±5 IRHD stretching 15 percent


R = inner diameter of the unstretched rubber ring

T = minimum wall thickness.

d_1 , D_m , L_m and l_1 are nominal dimensions.

Table 10B Spigot and Socket Dimensions for NP4 Unreinforced Pipes Made by Casting Process
(Clause 5.3)

All dimensions in millimetres

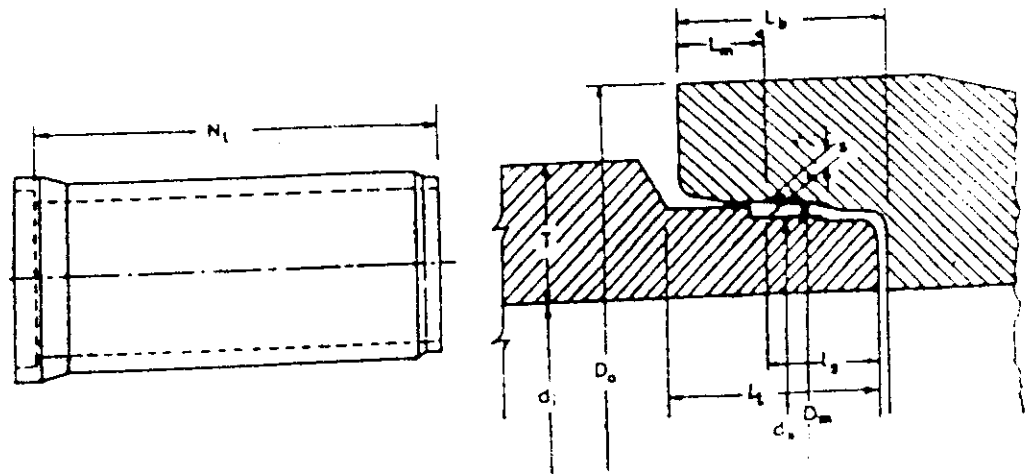

d_1	C	R	T	D_0	L_0	L_1	d_2	D_m	L_2	L_3	S
300±4	13	322	50	487±4	112±4	105±2	370.07	385.07	43	50	8.00±1.0
350±5	13	370	55	555±4	112±4	105±2	425.07	441.07	43	50	8.00±1.0
400±5	13	417	60	615±4	112±4	105±2	480.07	496.07	43	50	8.00±1.0
450±5	13	465	65	680±4	112±4	105±2	536.07	552.07	49	50	8.00±1.0
500±5	13	513	70	735±4	112±4	105±2	590.07	606.07	49	50	8.00±1.0
600±5	13	609	75	850±4	112±4	105±2	700.07	716.07	49	50	8.00±1.0
700±7	18	706	85	980±5	141±5	132±3	808.00	830.00	61	65	11.00±1.2
800±7	18	803	95	1100±5	141±5	132±3	924.00	946.00	61	65	11.00±1.2
900±7	18	901	100	1215±5	141±5	132±3	1036.00	1058.00	61	65	11.00±1.2
1000±7	18	998	115	1330±5	141±5	132±3	1148.00	1170.00	61	65	11.00±1.2
1100±7	24	1097	125	1520±6	155±6	145±3	1262.00	1291.30	72	65	14.65±1.5
1200±7	24	1195	135	1640±6	155±6	145±3	1372.48	1411.76	72	65	14.65±1.5
1400±10	24	1383	155	1870±6	155±6	145±3	1590.91	1620.21	72	65	14.65±1.5
1600±10	24	1578	180	2100±6	155±6	145±3	1814.91	1844.21	72	65	14.65±1.5
1800±10	24	1774	205	2340±6	155±6	145±3	2040.00	2069.30	72	65	14.65±1.5

C = diameter of the unstretched rubber chord, hardness 40±5 IRHD stretching 15 percent

S = inner diameter of the unstretched rubber ring

T = minimum wall thickness

L_0 , L_1 and L_2 are in millimetres

(Amendment No. 2, Note 2 of Table 15 and Note 3 of Table 16) — Substitute the following for the existing Note:

'Soft grade mild steel wire may be used as reinforcement for collars of pipes of nominal internal diameter up to 250 mm only by increasing the weight by a factor of 1.0784. Where only soft grade mild-steel wire is used for making collar cages, the weight of reinforcement shall be total weight of col 6 and 7 multiplied by 1.0784. This is allowed as a process requirement.'

(Amendment No. 2, Table 16, Note 1) — Insert the following at the end of Note 1:

'The details of mild steel collars shall be as follows:

Nominal Internal Diameter of Pipe

Steel Collar Dimensions

mm	Caulking Space, Min	Thickness, Min	Length, Min
	mm	mm	mm
2 200	22	6	250
2 400	22	6	250
2 600	22	6	250

(Page 20, clause 6.3, second and third sentences) — Substitute the following for the existing sentences:

'The cages shall consist of spirals or circular rings and straights of hard-drawn steel wire or mild steel rod. Reinforcement cages shall be placed symmetrically with respect to the thickness of the pipe wall.'

(Page 20, clause 6.4.1, first sentence) — Insert the following at the end of first sentence:

'or 53 grade ordinary Portland cement.'

(Page 20, clause 7.1):

a) Insert the following at the end of first sentence:

'If however, in case of pipes manufactured by casting process, the internal diameter, wall thickness, the minimum reinforcement (in case of reinforced pipes) and strength test requirements for different classes of pipes shall be as given in Tables 3A, 3B, 4A and 4B.'

b) Insert the following at the end of the clause:

'For collar jointed class NP3 and NP4 pipes of nominal internal diameter 900 mm and above, the effective length may also be 1.25 m.'

(Page 21, Note under clause 7.2) — Insert the following at the end:

'in case of pipes manufactured by spinning process.'

(Page 21, clause 8.2) — Substitute the following for the existing clause:

'8.2 Deviation from Straight — The deviation from straight in any pipe throughout its effective length, tested by means of a rigid straight edge as described in IS 3597:1998¹ shall not exceed, for all diameters, 3 mm for every metre run.'

(Page 21, clause 9.1.1, first sentence) — Substitute the following for the existing sentence:

'During manufacture, tests on compressive strength of concrete cubes shall be done as described in IS 516 : 1959². For pressure pipes splitting tensile strength tests of concrete cylinders shall be carried out as described in IS 5816 : 1999³.'

(Page 21, footnotes under clause 9.1.1) — Substitute the following for the existing footnotes:

¹Method of test for concrete pipes (second revision).

²Method of test for strength of concrete.

³Method of test for splitting tensile strength of concrete (first revision).

(Page 21, clause 9.2) — Substitute the following for the existing clause:

'9.2 The specimens of pipes selected in accordance with 9.1 shall be subjected to the following tests in accordance with IS 3597 : 1998¹:

a) Hydrostatic test,

- b) Three-edge bearing test, and
- c) Permeability test.

(Page 21, clauses 9.2.1 and 9.2.2) — Substitute the following for the existing clauses :

9.2.1 Permeability test when conducted in accordance with the method described in IS 3597 : 1998, shall satisfy the following requirements. The tests shall be done on outside surface of pipe at two places as shown in Fig. 5.

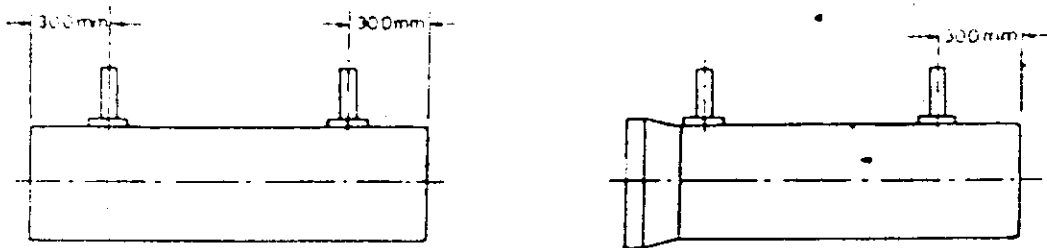


FIG. 5 PERMEABILITY TEST

9.2.1.1 Initial absorption

The drop of water level in the stand pipe at the end of 2 h is the initial absorption. This shall not exceed 1.5 cm and the difference in any two readings shall not be more than 0.5 cm³.

9.2.1.2 Final permeability

Fill the water in the stand pipe again up to the mark and take readings at half-hour interval up to 4 h. Absorption in the fourth hour is the final permeability. The average reading of two tests conducted on a pipe shall be expressed in cm³ and this shall not exceed 0.3 cm³.

(Page 21, footnote at the end of the page) — Substitute the following for the existing footnote.

“Methods of test for concrete pipes (recurrent test)”

Reinforcement Details

NP2 CLASS

1991

Dia of pipe (mm)	Web thickness mm	Longitudinal nos	Steel Weight (kg)	Spiral (kg)	Total weight (kg)	Total weight with cross ST	Cement per pipe (bag)	Weight of pipe (kg)	C.M.T
900	55	8	3.05	23.125	26.175	26.700	2.97	990	0.4125
1000	60	8	4.40	26.725	31.125	31.800	3.59	1198	0.4986
1100	65	8	4.40	31.850	36.250	37.000	4.28	1427	0.5944
1200	70	8	4.40	38.675	43.075	43.800	5.02	1675	0.6972
1400	75	12	6.60	51.425	58.025	59.100	6.25	2086	0.8680
1600	80	8+8	8.80	63.500	72.300	73.700	7.69	2534	1.0555
1800	90	8+8	8.80	81.850	90.650	92.000	9.61	3209	1.3347
2000	100	12+12	13.20	112.850	126.050	128.100	15.54	4145	1.6485
2200	110	12+12	13.20	140.925	154.125	156.100	17.96	4788	1.994

NP3 CLASS

1991

Dia of pipe (mm)	Web thickness mm	Longitudinal nos	Steel Weight (kg)	Spiral (kg)	Total weight (kg)	Total weight with cross ST	Cement per pipe (bag)	Weight of pipe (kg)	C.M.T
900	100	6+6	6.650	45.750	52.400	53.400	5.65	1884	0.7847
1000	115	6+6	6.650	53.800	60.450	61.500	7.24	2416	1.0055
1100	115	6+6	6.650	69.975	76.625	77.700	7.90	2640	1.0958
1200	120	8+8	8.875	83.925	92.800	94.200	8.95	2984	1.2430
1400	135	8+8	8.875	115.525	124.400	125.830	11.71	3904	1.6264
1600	140	8+8	8.875	163.500	172.375	173.800	13.76	4589	1.9111
1800	150	12+12	23.400	217.750	241.150	244.700	16.53	5510	2.2958
2000	170	12+12	23.400	244.750	268.150	272.000	20.85	6948	2.90
2200	185	12+12	23.400	283.250	306.650	310.200	24.94	8314	3.46


NP4 CLASS

1991

Dia of pipe (mm)	Web thickness mm	Longitudinal nos	Steel Weight (kg)	Spiral (kg)	Total weight (KG)	Total weight with cross ST	Cement per pipe (bag)	Weight of pipe (kg)	C.M.T
900	100	6+6	8.600	67.830	76.430	77.800	5.65	1884	0.7847
1000	115	8+8	15.100	88.700	103.800	106.100	7.24	2416	1.0055
1100	115	8+8	15.100	109.400	124.500	126.800	7.90	2640	1.0958
1200	120	8+8	15.100	132.670	147.770	150.100	8.95	2984	1.2430
1400	135	8+8	23.400	194.050	217.450	221.000	11.71	3904	1.6264
1600	140	12+12	23.400	272.425	295.820	299.400	13.76	4589	1.9111
1800	150	12+12	37.200	375.550	412.750	418.300	16.53	5510	2.2958
2000	170	12+12	37.200	379.475	416.675	422.300	20.85	6948	2.90
2200	185	12+12	37.200	402.250	439.450	445.100	24.94	8314	3.46

Size of collar.	42	46	50	54	60	1268	1478	1708	1918	2138
Cement.	0.264	0.322	0.360	0.424	0.564	0.360	0.526	0.646	0.903	1.011
Steel.	2.280	2.580	3.420	4.440	5.580	3.420	5.580	7.220	9.670	13.150



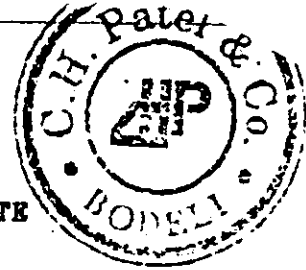

AMENDMENT NO. 2 APRIL 1991
TO
IS 458:1988 SPECIFICATION FOR PRECAST CONCRETE
PIPES (WITH AND WITHOUT REINFORCEMENT)
(Third Revision)

[Page 1, clause 0.3.1 (c)] - Substitute the following for the existing matter:

(c) In this revision a new classification of pipes has been followed. In respect of strength test, the new classes compare with the old classification as follows:

Class NP1	Same as class NP1 of earlier standard
Class NP2	Equivalent to class NP2 of earlier standard
Class NP3	New class introduced in this revision
Class NP4	Equivalent to class NP3 and NP4 of earlier standard
Class P1,P2 and P3	Same as class P1,P2 and P3 of earlier standard

Longitudinal and spiral reinforcement for different classes of pipes and three edge bearing test load of class NP2 pipes have been modified in this revision. Reinforcement to be provided in socket of different classes of pipes for rubber ring joint have also been included. Pipes suitable for railway loading are not included in this standard at present and this might be included at a later stage. The present class NP4 pipes shall not be used for railway loading.


(Page 2, clause 1.1) - Insert the following at the end:

The requirements for collars are also covered by this standard.

NOTE - In addition to the requirements specified specifically for the collars, the requirements given in the following clauses shall also apply for collars:

4.2, 4.3, 4.4, 4.5, 4.5.1, 4.5.3, 4.5.4, 6.1, 6.2, 6.2.1, 6.2.2, 6.3, 6.3.1, 6.4, 7.2, 8.1, 8.1.1, 8.1.2, 8.1.3, 8.1.4, 11.1 and 11.1.1.

(Page 2, clause 3.1) - Delete 'such as, railway loading' from line 16 and 17 of column 3 of the informal table.

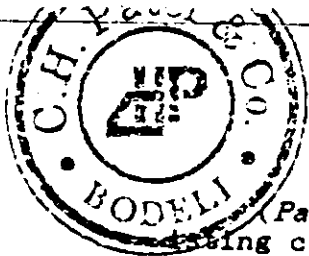

(Page 3, clause 4.3) - Substitute the following for the existing clause:

4.3 **Aggregates** - Aggregates used for manufacture of unreinforced and reinforced concrete pipes shall conform to 3 of IS 383:1970⁷. The maximum size of aggregate should not exceed one third the thickness of the pipe or 20 mm, whichever is smaller for pipes above 250 mm internal diameter. But for pipes of internal diameter 80 to 250 mm the maximum size of aggregate should be 10 mm.

NOTE - It is preferable to have the size and grading of aggregates conforming to IS 383:1970⁷. It is also preferable that materials finer than 75 micron IS Sieve is restricted to 3.0 percent by mass.

(Page 4, clause 5.2) - Insert the following as a new para:

For non-welded cages spiral reinforcement of the same diameter shall be closely spaced at the end of the pipe for a length of 150 mm to minimize damage during handling. The spacing of such end spirals shall not exceed 50 mm or half the pitch whichever is less. Such spiral reinforcement at ends shall be part of the total spiral reinforcement specified in different tables.

(Page 4, clause 5.2.2) - Insert 'subject to the requirements of 5.2.2.1.' at the end and insert a new clause 5.2.2.1 as follows:

5.2.2.1 Tolerances given in IS 432(Part 1):1982², IS 432(Part 2):1982³, IS 226:1975⁴ and IS 1786:1985⁵ shall be applied to the minimum mass of longitudinal reinforcement specified in different tables. Total mass of longitudinal reinforcement shall be calculated taking into account the clear cover provided at each end of the pipe.

NOTE - For longitudinal reinforcement conforming to IS 432 (Part 2): 1982³, tolerance, on mass shall be calculated from the diameter tolerance.

(Page 4, Footnote) - Insert the following new footnotes:

²Specification for mild steel and medium tensile steel bars and hard-drawn steel wire for concrete reinforcement Part 1 Mild steel and medium tensile steel bars (*third revision*).

³Specification for mild steel and medium tensile steel bars and hard-drawn steel wire for concrete reinforcement Part 2 Hard-drawn steel wire (*third revision*)

4Specification for structural steel (standard quality) (fifth revision).

5Specification for high strength deformed steel bars and wires for concrete reinforcement (third revision).

(Page 4, clause 5.3, second, third and fourth sentence) - Substitute the following for the existing sentences:

'Dimensions of collars shall be according to details given in Tables 1, 15 and 16. The reinforcement for the collars shall be as given in Table 15 and 16. The ends of collar reinforcement shall have a full ring at both ends.'


(Page 7, Table 2) -


- 1) Delete col (4), (5), (6) and (10)
- 2) Substitute '0.59' for '0.33' in col (8)
- 3) Substitute '0.16' for '0.10' and '0.18' for '0.12' in Sl No 1 and 2 respectively of col (9)
- 4) Substitute '12 or 8+8' for '8+8' in Sl No 20 and 21 of col (7)
- 5) Substitute '2.5 m' for '2 m' in Note 3.
- 6) Insert the following new Note:

'NOTE - Total mass of longitudinal reinforcement shall be calculated by multiplying the values given in column 8 by the length of the pipe and then deducting for the cover length provided at the two ends.'

(Page 8, Table 3) -

- 1) Substitute '0.59' for '0.33' in col (4)
- 2) Substitute '0.16' for '0.15' in Sl No 1 of col (5)
- 3) Substitute '8 or 6+6' for '6+6' in Sl No 12, 13 and 14 of col (3)
- 4) Substitute '2.5 m' for '2 m' in Note 3
- 5) Delete Note 2 and renumber the subsequent Notes.
- 6) Delete 'and a minimum cement content of 400 kg/m³' from Note 4.

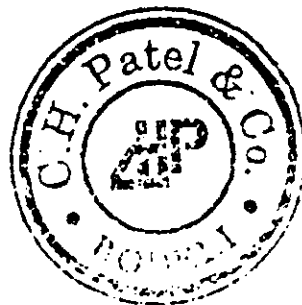

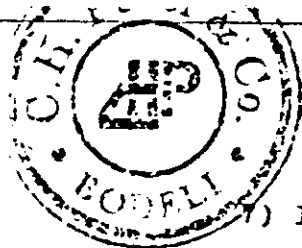

7) Insert the following new Note:

NOTE - Total mass of longitudinal reinforcement shall be calculated by multiplying the values given in col 4 by the length of the pipe and then deducting for the cover length provided at the two ends.

(Page 9, Table 4) - Insert the following as Table 4:

TABLE 4 : DESIGN AND STRENGTH TEST REQUIREMENTS OF CONCRETE PIPES OF CLASS NP4 - REINFORCED CONCRETE, HEAVY-DUTY, NON-PRESSURE PIPES (Clauses 5.1.1, 5.1.2 5.1.3, 5.2.2, 6.3.2, and 7.1)

NOMINAL INTERNAL DIAMETER OF PIPES	BARREL WALL THICKNESS	REINFORCEMENTS		STRENGTH TEST REQUIREMENTS FOR THREE EDGE BEARING TEST		
		Longitudinal, Mild steel or Hard-Drawn Steel	Spiral, Hard-drawn Steel	Load to Produce 0.25 mm Crack	Ultimate Load	
(1) mm	(2) mm	(3) Min Number	(4) kg/linear metre	(5) kg/linear metre	(6) kN/linear metre	(7) kN/linear metre
80	25	6	0.59	0.24	22.1	33.15
100	25	6	0.59	0.36	22.1	33.15
150	25	6	0.59	0.74	23.3	34.95
200	30	6	0.59	1.30	24.6	36.9
225	30	6	0.59	1.64	25.2	37.8
250	30	6	0.59	1.98	25.5	38.25
300	40	8	0.78	2.71	26.4	39.6
350	75	8	0.78	3.14	29.8	44.7
400	75	8	0.78	3.52	33.9	50.9
450	75	8	0.78	3.88	36.9	55.3
500	75	8	0.78	5.96	40.0	61.2
600	85	8 or 6+6	2.34	9.63	46.3	69.4
700	85	8 or 6+6	3.44	14.33	52.2	78.3
800	95	8 or 6+6	3.44	21.20	59.3	89.1
900	100	6+6	3.44	27.13	66.3	99.4
1000	115	8+8	6.04	35.48	72.6	108.9
1100	115	8+8	6.04	43.76	80.4	120.6
1200	120	8+8	6.04	53.07	88.3	132.4
1400	135	8+8	9.36	77.62	104.2	156.4
1600	140	12+12	9.36	108.97	119.6	179.5
1800	150	12+12	14.88	150.22	135.3	203.0
2000	170	12+12	14.88	151.79	135.3	203.0
2200	185	12+12	14.88	160.90	142.2	213.3
2400	200	12+12	14.88	216.96	155.0	232.5
2600	215	12+12	14.88	258.93	166.7	250.0

NOTE 1 - The actual internal diameter is to be declared by the manufacturer and tolerance is to be applied on the declared diameter (see also 0.3.2)

NOTE 2 - The longitudinal reinforcement given in this table is valid for pipes up to 2.5 m effective length for internal dia of pipe up to 250 mm and 3 m effective length for higher diameter pipes.

NOTE 3 - Concrete for pipes above 1800 mm nominal diameter shall have a minimum compressive strength of 35 N/mm² at 28 days.

NOTE 4 - If mild steel is used for spiral reinforcement the weight specified in col 5 shall be increased by a factor 140/125.

NOTE 5 - Total mass of longitudinal reinforcement shall be calculated by multiplying the values given in col 4 by the length of the pipe and then deducting for the cover length provided at the two ends.

(Page 9, Table 5) -

- 1) Substitute '0.59' for '0.33' in col (4)
- 2) Substitute '0.16' for '0.15' in Sl No 1 of col (5)
- 3) Substitute '2.5 m' for '2 m' in Note 4
- 4) Insert the following new Note:

'NOTE - Total mass of longitudinal reinforcement shall be calculated by multiplying the values given in col 4 by the length of the pipe and then deducting for the cover length provided at the two ends.'

(Page 10, Table 6) -


- 1) Substitute '0.59' for '0.33' in col (4)
- 2) Substitute '8 or 6+6' for '6+6' in Sl No 14 and 15 of col (3)
- 3) Substitute '2.5 m' for '2 m' in Note 4
- 4) Insert the following new Note:

'NOTE - Total mass of longitudinal reinforcement shall be calculated by multiplying the values given in column 4 by the length of the pipe and then deducting for the cover length provided at the two ends.'

(Page 11, Table 7) -

- 1) Substitute '0.59' for '0.33' in col (4)
- 2) Substitute '8 or 6+6' for '6+6' in Sl No 12 of col (3)
- 3) Substitute '2.5 m' for '2 m' in Note 4
- 4) Insert the following new Note:

'NOTE - Total mass of longitudinal reinforcement shall be calculated by multiplying the values given in col 4 by the length of the pipe and then deducting for the cover length provided at the two ends.'

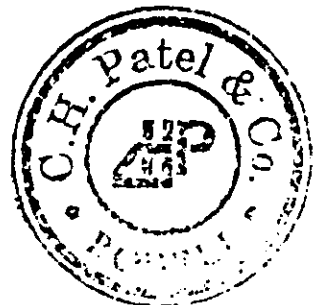

(Page 13, Table 9, Note 2) - Substitute the following for the existing note:

NOTE 2 - The dimensions *DS2*, *DS3*, *LSP*, *TS*, *T*, *H*, *S*, *HT* and *K* shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

<i>Dimensions</i>	<i>Tolerances</i>
<i>DS2, DS3 & LSP</i>	The tolerances shall be as given below:

<i>Chord Dia- meter mm</i>	<i>Toler- ence for DS2 mm</i>	<i>Toler- ence for DS3 mm</i>	<i>Toler- ence for LSP mm</i>
11	± 2	± 3	± 4
12	± 2	± 3	± 4
16	± 2.5	± 3.5	± 5
20	± 3	± 4	± 5.5
22	± 3.5	± 4.5	± 6
25	± 4	± 5	± 7

<i>T and HT</i>	Same as that of wall thickness given in 7.2
-----------------	---


<i>TS and H</i>	Half the tolerance on wall thickness given in 7.2
-----------------	---


<i>K and S</i>	The tolerances shall be as given below:
----------------	---

<i>Chord Diameter mm</i>	<i>Tolerance for K mm</i>	<i>Tolerance for S mm</i>
11	± 1.25	± 0.75
12	± 1.25	± 0.75
16	± 2.00	± 1.25
20	± 2.25	± 1.50
22	± 2.75	± 1.50
25	± 3.25	± 2.00

(Page 14, Table 10, Note 2) - Substitute the following for the existing Note :

NOTE 2 - The dimensions *DS2*, *DS3*, *LSP*, *TS*, *T*, *H*, *S*, *HT* and *K* shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

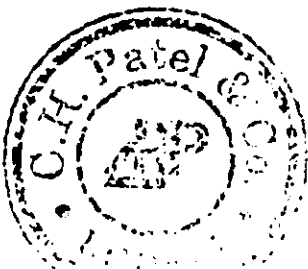

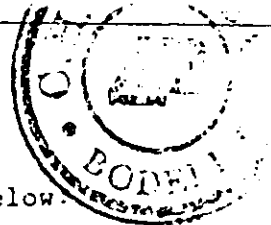

Dimensions

Tolerances

*DS2, DS3
& LSP*

The tolerances shall be as given below.

<i>Chord Diameter</i> mm	<i>Tolerance for DS2,</i> mm	<i>Tolerance for DS3,</i> mm	<i>Tolerance for LSP,</i> mm
11	± 2	± 3	± 4
12	± 2	± 3	± 4
16	± 2.5	± 3.5	± 5
20	± 3	± 4	± 5.5
22	± 3.5	± 4.5	± 6
25	± 4	± 5	± 7

T and HT

Same as that of wall thickness given in 7.2

TS and H

Half the tolerance on wall thickness given in 7.2

K and S

The tolerances shall be as given below:

<i>Chord Diameter</i> mm	<i>Tolerance for K -</i> mm	<i>Tolerance for S</i> mm
11	± 1.25	± 0.75
12	± 1.25	± 0.75
16	± 2.00	± 1.25
20	± 2.25	± 1.50

(Page 15, Table 11, Note 2) - Substitute the following for the existing note:

NOTE 2 - The dimensions *LS, LSP, T, TS, H, L, K* and *b* shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

Dimensions

Tolerances

LS & LSP

± 7 mm

T


Same as that of wall thickness given in 7.2

<i>H</i> and <i>TS</i>	Half the tolerance on wall thickness given in 7.2
<i>L</i>	± 0.5 mm
<i>b</i>	± 1 mm for 28 mm and ± 1.5 mm for 35 mm
<i>K</i>	± 1.75 mm for 20 mm rubber ring chord diameter and ± 2.5 mm for 25 mm rubber ring chord diameter.

(Page 16, Table 12, Note 2) - Substitute the following for the existing Note:

NOTE 2 - The dimensions *DS2*, *DS3*, *LSP*, *TS*, *T*, *H*, *S*, *HT* and *K* shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

<i>Dimensions</i>	<i>Tolerances</i>		
<i>DS2</i> , <i>DS3</i>	The tolerances shall be as given below:		
<i>LSP</i>	<i>Chord Diameter</i>	<i>Tolerance for DS2</i>	<i>Tolerance for DS3</i>
	mm	mm	mm
	11	± 2	± 3
	12	± 2	± 3
	16	± 2.5	± 3.5
	20	± 3	± 4
	22	± 3.5	± 4.5
25	± 4	± 5	
<i>T</i> and <i>HT</i>	Same as that of wall thickness given in 7.2		
<i>TS</i> and <i>H</i>	Half the tolerance on wall thickness given in 7.2		
<i>K</i> and <i>S</i>	The tolerances shall be as given below:		
<i>Chord Diameter</i>	<i>Tolerance for K</i>	<i>Tolerance for S</i>	
mm	mm	mm	
11	± 1.25	± 0.75	
12	± 1.25	± 0.75	
16	± 2.00	± 1.25	
20	± 2.25	± 1.50	
22	± 2.75	± 1.50	

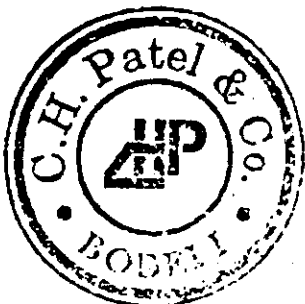



(Page 17, Table 13, Note 2) - Substitute the following for the existing note:

NOTE 2 - The dimensions *DS2*, *DS3*, *LSP*, *TS*, *T*, *H*, *S*, *HT* and *K* shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

<i>Dimensions</i>	<i>Tolerances</i>		
<i>DS2</i> , <i>DS3</i> & <i>LSP</i>	The tolerances shall be as given below:		
	<i>Chord Diameter</i>	<i>Tolerance for DS2</i>	<i>Tolerance for DS3</i>
	mm	mm	mm
	11	± 2	± 3
	12	± 2	± 3
	16	± 2.5	± 3.5
	20	± 3	± 4
	22	± 3.5	± 4.5
	25	± 4	± 5
<i>T</i> and <i>HT</i>	Same as that of wall thickness given in 7.2		
<i>TS</i> and <i>H</i>	Half the tolerance on wall thickness given in 7.2		
<i>K</i> and <i>S</i>	The tolerances shall be as given below:		
	<i>Chord Diameter</i>	<i>Tolerance for K</i>	<i>Tolerance for S</i>
	mm	mm	mm
	11	± 1.25	± 0.75
	12	± 1.25	± 0.75
	16	± 2.00	± 1.25
	20	± 2.25	± 1.50

(Page 19, Table 14) - Insert the following new tables after table 14:

TABLE 15 DESIGN REQUIREMENTS OF REINFORCED CONCRETE COLLARS FOR PIPES OF CLASS NP2
(Clause 5.3)

NOMINAL INTERNAL DIAMETER OF PIPE	COLLAR DIMENSIONS			REINFORCEMENTS		
	Min Caulking Space	Min Thick- ness	Min Len- gth	Longitudinal, Mild Steel or Hard-drawn Steel Min. nos.	Mild Steel Weight (6) kg per collar	Spiral, Hard- drawn Steel (7) kg per collar
(1) mm.	(2) mm.	(3) mm.	(4) mm.	(5)	(6)	(7)
80	13	25	150	6	0.08	0.07
100	13	25	150	6	0.08	0.08
150	13	25	150	6	0.08	0.10
200	13	25	150	6	0.08	0.12
225	13	25	150	6	0.08	0.14
250	13	25	150	6	0.08	0.16
300	16	30	150	8	0.11	0.22
350	16	32	150	8	0.11	0.25
400	16	32	150	8	0.11	0.27
450	19	35	200	8	0.15	0.40
500	19	35	200	8	0.15	0.60
600	19	40	200	8	0.15	0.70
700	19	40	200	8	0.23	1.05
800	19	45	200	8	0.23	1.85
900	19	50	200	8	0.23	2.05
1000	19	55	200	8	0.33	2.25
1100	19	60	200	8	0.33	3.09
1200	19	65	200	8	0.33	4.11
1400	19	75	200	12	0.50	5.08
1600	19	80	200	12 or 8+8	0.67	6.55
1800	19	90	200	12 or 8+8	0.67	9.00
2000	19	100	200	12+12	1.00	12.15
2200	19	110	200	12+12	1.00	13.30

NOTE 1 - If mild steel is used for spiral reinforcement the weight specified in col 7 shall be increased by a factor 140/125.

NOTE 2 - Soft grade mild steel wire for spirals may be used for collars of pipes of internal diameter up to 150 mm only by increasing weight by a factor 140/84.

NOTE 3 - Internal diameter of collar to suit the actual diameter of pipes with minimum caulking space as given in col 2.

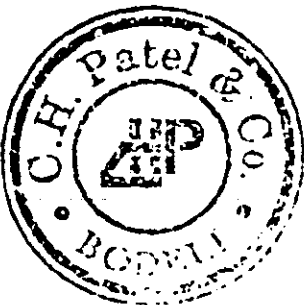


TABLE 16 DESIGN REQUIREMENTS OF REINFORCED CONCRETE COLLARS FOR PIPES OF NP3 AND NP4 CLASS
(Clause 5.3)

NOMINAL INTERNAL DIAMETER OF PIPE	COLLAR DIMENSIONS			REINFORCEMENTS		
	Min. Caulking Space	Min. Thick-ness	Min. Len-gth	Longitudinal, Mild Steel or Hard-drawn Steel Min. nos.	Weight (6) kg per collar	Spiral, Hard drawn Steel (7) kg per collar
(1) mm.	(2) mm.	(3) mm.	(4) mm.	(5)	(6)	(7)
80	13	25	150	6	0.08	0.07
100	13	25	150	6	0.08	0.08
150	13	25	150	6	0.08	0.10
200	13	25	150	6	0.08	0.12
225	13	25	150	6	0.08	0.14
250	13	25	150	6	0.08	0.16
300	16	30	150	8	0.11	0.22
350	19	35	200	8	0.15	0.40
400	19	35	200	8	0.15	0.50
450	19	35	200	8	0.15	0.60
500	19	40	200	8	0.15	0.70
600	19	40	200	8	0.23	1.05
700	19	45	200	8	0.23	1.85
800	19	50	200	8	0.23	2.05
900	19	55	200	8	0.33	2.25
1000	19	60	200	8	0.33	3.09
1100	19	65	200	8	0.33	4.11
1200	19	75	200	12	0.50	5.08
1400	19	80	200	12 or 8+8	0.67	6.55
1600	19	90	200	12 or 8+8	0.67	9.00
1800	19	100	200	12+12	1.00	12.15
2000	19	110	200	12+12	1.00	13.30

NOTE 1 - Collars for sizes 2200 mm and above shall be made out of mild steel plate of 6 mm thickness, steel conforming to IS 226:1975 with outside painted.

NOTE 2 - If mild steel is used for spiral reinforcement, the weight specified in col 7 shall be increased by a factor 140/125.


NOTE 3 - Soft grade mild steel wire for spirals may be used for collars of pipes of internal diameter up to 150 mm only by increasing weight by a factor 140/84.

(Page 20, Clause 6.2.2) - Delete and renumber 6.2.3 as 6.2.2

(Page 20, Clause 6.3.1, First sentence)

1) Substitute the following for the first sentence:

Pipes having barrel thickness 100 mm and above shall have double reinforcement cage and the amount of spiral steel in the outer cage shall be 75 percent of the mass of spiral steel in the inner cage, whilst the total shall conform to the requirements specified in the relevant tables of this standard.

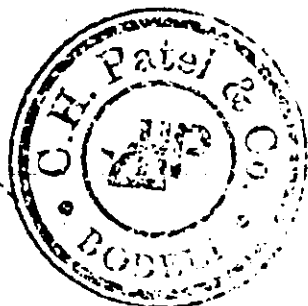

The mass of longitudinals in the outer cage and inner cage should be the same, that is equal to half the total mass of longitudinals specified in the relevant tables.

2) Insert the following Note below the clause:

NOTE - It is preferable that single reinforcement cage should be located near the inner surface of the pipe with adequate clear cover.

(Page 20, Clause 6.3.2, Last sentence) - Substitute the following for the last sentence:

'Diagonal reinforcement is a process requirement and shall not be counted against longitudinal and spiral reinforcement.'

(Page 20, Clause 6.3.3) - Delete

(Page 20, Clause 7.2) - Delete 'or socket' in 7.2 (b) and substitute the following for 7.2 (c):

'c) Wall thickness:

1) Up to and including 30 mm	+ 2 mm - 1 mm
2) Over 30 mm and up to and including 50 mm	+ 3 mm - 1.5 mm
3) Over 50 mm and up to and including 65 mm	+ 4 mm - 2 mm
4) Over 65 mm and up to and including 80 mm	+ 5 mm - 2.5 mm
5) Over 80 mm and up to and including 95 mm	+ 6 mm - 3 mm
6) Over 95 mm	+ 7 mm - 3.5 mm


(Page 20, Clause 7.1, Last sentence) - Substitute the following for the last sentence:

'For collar jointed pipes effective length shall be 2 m or 2.5 m up to 250 mm nominal diameter pipes and 2.5, 3.0, 3.5 or 4.0 m for pipes above 250 mm nominal diameter.'

(Page 21, clause 10.1.3 and Table 15) - Substitute 'Table 17' for 'Table 15'

(Page 22, Clause 10.2.1.1 and 10.2.2) - Substitute 'Table 17' for 'Table 15'

(CED 2)

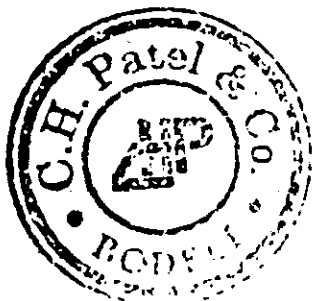

IS 458 : 1988

Indian Standard
SPECIFICATION FOR
PRECAST CONCRETE PIPES
(WITH AND WITHOUT REINFORCEMENT)
(*Third Revision*)



Second Reprint AUGUST 1997


UDC 621.643.2 [666 972]

© Copyright 1989
BUREAU OF INDIAN STANDARDS
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI 110002

Gr 9 + 1

May 1989

2V-9.VV



IS : 458 - 1988

Indian Standard

SPECIFICATION FOR PRECAST CONCRETE PIPES (WITH AND WITHOUT REINFORCEMENT) (Third Revision)

0. FOREWORD

0.1 This Indian Standard (Third Revision) was adopted by the Bureau of Indian Standards on 15 November 1988, after the draft finalized by the Cement and Concrete Sectional Committee had been approved by the Civil Engineering Division Council.

0.2 Reinforced cement concrete pipes are widely used for water mains, sewers, culverts and in irrigation. When used for carrying highly acidic sewage or industrial wastes, necessary precautions shall have to be taken against chemical attack and corrosion. This standard lays down the requirements of quality and dimensions of concrete pipes to serve as guidance to the manufacturers and users in producing and obtaining concrete pipes of suitable quality. Guidance regarding laying of concrete pipes is given in IS : 783-1985¹.

0.3 This standard was first published in 1956 and subsequently revised in 1961 and 1971. The present revision has been taken up with a view to incorporating the modifications found necessary as a result of experience gained with the use of this standard. The title of the standard has been modified as 'Specification for precast concrete pipes (with and without reinforcement)'.

0.3.1 This revision incorporates a number of changes, the most important of them being:


- a) Allowing the use of cements conforming to IS : 8041-1978², IS : 8043-1978³ and IS : 8112-1976⁴ for the manufacture of concrete pipes;
- b) Allowing the use of wire fabric conforming to IS : 1566-1982⁵, deformed bars and wires

conforming to IS : 1786-1985¹ and structural steel bars conforming to IS : 226-1975² for manufacture of concrete pipes;

- c) Class NP4 pipes given in the earlier standard have been deleted and class NP3 pipes of the earlier standard have been re-designated as class NP4 after incorporating a new class, medium-duty non-pressure pipes which have been designated as class NP3. The table for the earlier class NP3 pipes, which in this revision have been re-designated as class NP4, has been modified so as to make it suitable for railway loading also and additional sizes have been included. Longitudinal and spiral reinforcement for different classes of pipes and three edge bearing test load of class NP2 pipes have also been modified in this revision. Reinforcement to be provided in socket of different classes of pipes for rubber ring joint have also been included in this revision;
- d) Inclusion of details for spigot and socket ends for all the classes of pipes and details of flush type joints for the non-pressure pipes;
- e) Inclusion of figures illustrating some typical arrangements of reinforcement in socket;
- f) Deletion of sand bearing test and bursting test from this standard. Bursting test has been replaced by splitting tensile strength test of concrete cylinders for pressure pipes;
- g) Modification in the length of pipes allowing the manufacturer to declare the effective length which shall be between 1'0 and 4'0 m;
- h) Modification in different design requirements of the pipes;
- j) Inclusion of larger diameter pipes for all classes of pipes except for class NP1 and P1;

¹Code of practice for laying of concrete pipes (first revision).
²Specification for rapid hardening Portland cement (first revision).
³Specification for hydrophobic Portland cement (first revision).
⁴Specification for 43 grade ordinary Portland cement.
⁵Specification for hard-drawn steel wire fabric for concrete reinforcement (second revision).

¹Specification for high strength deformed steel bars and wires for concrete reinforcement (third revision).
²Specification for structural steel (standard quality) (fifth revision).



- k) Inclusion of a clause on repair of pipes; and
- m) Modification in sampling and inspection of pipes.

should be treated as actual internal diameters tolerances specified in this standard and such modifications should be made suitable for manufacturing pipes with flexible rubber ring joints.

0.3.2 In order to accommodate the existing moulds used by the manufacturers for manufacturing class NP3 pipes given in the earlier standard, the diameters of class NP3 and NP4 pipes in this revision have been given as nominal internal diameters. The actual internal diameters of these pipes are, therefore, to be declared by the manufacturers. However, the manufacturers should gradually change their moulds as it has been desired that after 1995, these nominal internal diameters

0.4 For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test, shall be rounded off in accordance with IS : 2-1960¹. The number of significant figures retained in the rounded off value should be the same as that of the specified value in this standard.

¹Rules for rounding off numerical values (revised)

1. SCOPE

1.1 This standard covers the requirements for reinforced and unreinforced precast cement concrete pipes, of both pressure and non-pressure varieties used for water mains, sewers, culverts and irrigation.

1.2 Prestressed concrete pipes and pipes with non-circular section are not covered by this standard.

2. TERMINOLOGY

2.0 For the purpose of this standard, the following definitions shall apply.

2.1 Working Pressure — It is the maximum sustained internal pressure excluding abnormal conditions such as surge (water hammer), to which the pipeline may be subjected when in use.

2.2 Site Test Pressure — It is the pressure to be applied to the pipeline or sections thereof, after laying, to test its strength and watertightness.

Note — The site test pressure to be imposed will have to be determined when placing orders for pipes and fittings. In general, this pressure should not be less than the maximum pipelines operating pressure plus the calculated surge pressure but in no case should exceed the hydrostatic test pressure.

2.3 Hydrostatic Test Pressure — It is the maximum pressure which the pipe can withstand without any leakage when tested for hydrostatic pressure in accordance with this standard and IS : 3597-1985¹.

2.4 Surge (Water Hammer) Pressure — It is the pressure which is produced by a change of velocity of the moving stream and becomes maximum when there is a sudden stoppage which may be caused by the closing of a valve or by shutting down a pump station.

3. CLASSIFICATION

3.1 For the purpose of this standard, concrete pipes shall be classified as under:

¹Methods of test for concrete pipes (first revision).

Class	Description	Conditions Where Normally Used
NP1	Unreinforced concrete non-pressure pipes	For drainage irrigation use, ground or in shallow trenches
NP2	Reinforced concrete, light-duty, non-pressure pipes	For drainage irrigation use, culverts carrying light traffic
NP3	Reinforced concrete, medium-duty, non-pressure pipes	For drainage irrigation use, culverts carrying medium traffic
NP4	Reinforced concrete, heavy-duty, non-pressure pipes	For drainage irrigation use, culvert carrying heavy traffic, gas, railway load
P1	Reinforced concrete pressure pipes tested to a hydrostatic pressure of 0.2 MPa (20 m head)	For use on gas mains, the site pressure not exceeding two-thirds hydrostatic test pressure
P2	Reinforced concrete pressure pipes tested to a hydrostatic pressure of 0.4 MPa (40 m head)	For use on public mains, the site pressure not exceeding half of the hydrostatic test pressure
P3	Reinforced concrete pressure pipes tested to a hydrostatic pressure of 0.6 MPa (60 m head)	do

Note — The uses are only by way of recommendations as a general guidance and the exact use to be decided by the engineer-in-charge.

3.2 Unreinforced and reinforced concrete non-pressure pipes shall be capable of withstanding pressure of 0.07 MPa (7 m head).

(I
'0.3
intern
diame
the ex
should
gradua
after I
diame
(P
the wo
(P
'Type
(P

(CED 2



diameters
and such mo
facturing p

er a partic
plied with
expressing
in accord
nificant pl
ld be the s
andard.

is (revised

ditions Wh
ormally Us

drainage
ion use,
i or in sh
es

dra ge
ion use,
s car
affic

drainage
on use
s car
n traffic

drainage
on use,
car

traffic,
way load

on g
the site
e not ex
o-thirds
tatic test

on pur
the sit
e r e
f of... h
est press

do

of recom
act usag

rete nor
anding

AMENDMENT NO. 1 JANUARY 1991
TO
IS 458 : 1988 SPECIFICATION FOR PRECAST
CONCRETE PIPES (WITH AND WITHOUT
REINFORCEMENT)

(Third Revision)

(Page 2, clause 0.3.2) — Insert the following new clause after 0.3.2:

'0.3.3 Because of increase in barrel wall thickness of class NP2 pipes of internal diameter 600 mm to 1 200 mm, both nominal and actual internal diameters have been specified for class NP2 pipes in order to accommodate the existing moulds. As it has been desired that all non-pressure pipes should have flexible rubber ring joints after 1995, the manufacturers should gradually change their moulds suitable for manufacturing such pipes and after 1995 nominal internal diameters should be treated as actual internal diameters.'


(Page 3, clause 4.5.2, line 3) — Insert the words 'not less than' after the words 'shall be'.

(Page 3, clause 4.6) — Substitute 'Type 2 of IS 5382 : 1985' for 'Type 1 A of IS 5382 : 1967'.

(Page 3, foot-note No. 4) — Insert '(second revision)' at the end.

(CED 2)





4. MATERIALS

4.1 For precast concrete pipes, materials complying with the requirements given in 4.2 to 4.6 shall be used.

4.2 Cement — Cement used for the manufacture of unreinforced and reinforced concrete pipes shall conform to IS : 269-1976¹ or IS : 455-1976² or IS : 1489-1976³ or IS : 8041-1978⁴ or IS : 8043-1978⁵ or IS : 8112-1976⁶.

NOTE — The use of pozzolana as an admixture to Portland cement is not permitted. Unless otherwise specified by the purchaser, the type of cement to be used is left to the discretion of the manufacturer.

4.3 Aggregates — Aggregates used for the manufacture of unreinforced and reinforced concrete pipes shall conform to IS : 383-1970⁷. The maximum size of aggregate should not exceed one third the thickness of the pipe or 20 mm, whichever is smaller.

4.4 Reinforcement — Reinforcement used for the manufacture of the reinforced concrete pipes shall be mild steel Grade I or medium tensile steel bars conforming to IS : 432 (Part 1)-1982⁸ or hard-drawn steel wire conforming to IS : 432 (Part 2)-1982⁹ or structural steel (standard quality) bars conforming to IS : 226-1975¹⁰. Where soft grade wire is used, it shall conform to IS : 280-1978¹¹.

NOTE — Wire fabric conforming to IS : 1566-1982¹² or deformed bars and wires conforming to IS : 1786-1985¹³ may also be used.

4.5 Concrete or Mortar — Concrete used for the manufacture of unreinforced and reinforced concrete pipes and collars shall conform to IS : 456-1978¹⁴.

¹Specification for ordinary and low heat Portland cement (third revision).

²Specification for Portland slag cement (third revision).

³Specification for Portland pozzolana cement (second revision).

⁴Specification for rapid hardening Portland cement (first revision).

⁵Specification for hydrophobic Portland cement (first revision).

⁶Specification for 43 grade ordinary Portland cement (first revision).

⁷Specification for coarse and fine aggregates from natural sources for concrete (second revision).

⁸Specification for mild steel and medium tensile steel bars and hard-drawn steel wires for concrete reinforcement: Part 1 Mild steel and medium tensile steel bars (third revision).

⁹Specification for mild steel and medium tensile steel bars and hard-drawn steel wires for concrete reinforcement: Part 2 Hard-drawn steel wire (third revision).

¹⁰Specification for structural steel (standard quality) (fifth revision).

¹¹Specification for mild steel wire for general engineering purposes (third revision).

¹²Specification for hard-drawn steel wire fabric for concrete reinforcement (second revision).

¹³Specification for high strength deformed steel bars and wires for concrete reinforcement (third revision).

¹⁴Code of practice for plain and reinforced concrete (third revision).

4.5.1 The concrete for non-pressure pipes shall have a minimum cement content of 360 kg/m³ and a minimum compressive strength of 20 N/mm² at 28 days. If mortar is used, it shall have a minimum cement content of 450 kg/m³ and a compressive strength not less than 20 N/mm² at 28 days. The concrete for pressure pipes shall have a minimum cement content of 450 kg/m³ and a minimum compressive strength of 25 N/mm² at 28 days. If mortar is used, it shall have a minimum cement content of 600 kg/m³ and a compressive strength not less than 25 N/mm² at 28 days.

Where the process of manufacture is such that the strength of concrete or mortar in the pipe differs from that given by tests on cubes, the two may be related by a suitable conversion factor. If the purchaser requires evidence of this factor, he shall ask for it before placing the order. The conversion factor for 28 days compressive strength for spun concrete may be taken as 1.25 in the absence of any data.

4.5.2 For pressure pipes splitting tensile strength of concrete cylinders at 28 days, when tested in accordance with IS : 5816-970¹, shall be 2.5 N/mm².

4.5.3 Compressive strength tests shall be conducted on 15 cm cubes in accordance with the relevant requirements of IS : 456-1978² and IS : 516-1959³.

4.5.4 The manufacturer shall give a certificate indicating the quantity of cement in the concrete mix.

4.6 Rubber Ring — Rubber ring chords used in pipe joints shall conform to Type 1A of IS : 5382-1967⁴.

5. DESIGN

5.1 General — Reinforced concrete pipes either spun or cast shall be designed such that the maximum tensile stress in the circumferential steel due to specified hydrostatic test pressure does not exceed the limit of 125 N/mm² in the case of mild steel rods, 140 N/mm² in the case of hard-drawn steel wires and high strength deformed steel bars and wires.


5.1.1 The barrel thickness shall be such that under the specified hydrostatic test pressure, the maximum tensile stress in concrete, when considered as effective to take stress along with the tensile reinforcement, shall not exceed 2 N/mm² but the wall thickness shall be not less than those given in Tables 1 to 7 subject to 7.2(c).

¹Method of test for splitting tensile strength of concrete cylinders.

²Code of practice for plain and reinforced concrete (third revision).

³Methods of test for strength of concrete.

⁴Specification for rubber sealing rings for gas mains, water mains and sewers.



5.1.2 Pipes of length above 3 m and up to 4 m may be supplied by agreement between the user and the supplier and for such pipes, the quantity of reinforcement shall be modified as below:

Longitudinal reinforcement — Reinforced cement concrete pipes of lengths up to 4 m may be accepted if the longitudinal reinforcement is increased in proportion to the square of length compared with what is used for 3 m length as specified in Tables 2 to 7.

For 'L' (in metre) length of pipe, longitudinal reinforcement shall be $\frac{L^2}{3^2}$ times the longitudinal reinforcement used for 3 m long pipes.

5.1.3 Longitudinal reinforcement shall be provided to ensure rigidity and correct location of cages (grids) longitudinally and to limit the effects of transverse cracking. Minimum longitudinal reinforcement shall be as given in Table 2 to 7.

5.2 Reinforcement — The reinforcement in the reinforced concrete pipe shall extend throughout the length of the pipe and shall be so designed that it may be readily placed and maintained to designed shape and in the proper position within the pipe mould during the manufacturing process. The circumferential and longitudinal reinforcement shall be adequate to satisfy the requirements specified under 5.1.

5.2.1 The pitch of circumferential reinforcement shall be not more than the following:

- a) 200 mm for pipes of nominal internal diameter 80 to 150 mm,
- b) 150 mm for pipes of nominal internal diameter 200 to 350 mm, and
- c) 100 mm for pipes of nominal internal diameter 400 mm and above.

The pitch shall also be not less than the maximum size of aggregate plus the diameter of the reinforcement bar used.

5.2.2 The quantity and disposition of steel in pipes may be decided by mutual agreement between the purchaser and the supplier; however, it shall be proved by calculations and tests that the quality of the pipes conforms to all the requirements specified in the standard. In the absence of calculations and tests, the reinforcement given in Tables 2 to 7 shall be used as minimum reinforcement.

5.2.3 If so required by the purchaser, the manufacturer shall give a certificate indicating the details relating to quality, quantity and dispersion of steel in the pipes as well as the clear cover to the steel provided in the pipe.

5.3 Ends of Pipes — The ends of concrete pipes shall be suitable for flush (see Fig. 1), collar (see Fig. 2), socket and spigot, roll on joints or confined gasket joints. Dimensions of collars shall be according to details given in Tables 1 and 2. The reinforcement for the collars shall be as given in Table 2. The ends of collar reinforcement shall have a full ring at both ends and the longitudinal reinforcement shall be proportional to the length of the collar. Dimensions of spigot and socket for unreinforced concrete pipes shall be as given in Table 8. Dimensions of spigot and socket for rubber ring roll on jointed pipes shall be as given in Tables 9 to 13. Reinforcement in socket of rubber ring jointed pipes shall be as given in Table 14.

NOTE 1 — Bends, junctions and specials for concrete pipes covered under this standard shall conform to the requirements of IS : 7322-1985¹.


NOTE 2 — All the joints in pressure pipes shall be flexible rubber ring joints by the end of the year 1990.

NOTE 3 — Some typical arrangements of reinforcement in socket are illustrated in Fig. 3 and 4.


5.3.1 The pipe joints shall be capable of withstanding the same pressures as the pipe.

NOTE — The requirement of 5.3.1 does not imply that the collar shall also be tested for the test pressure for pipes specified in 3.1, 3.2 and 9.2.

¹Specification for specials for steel cylinder reinforced concrete pipes (first revision).

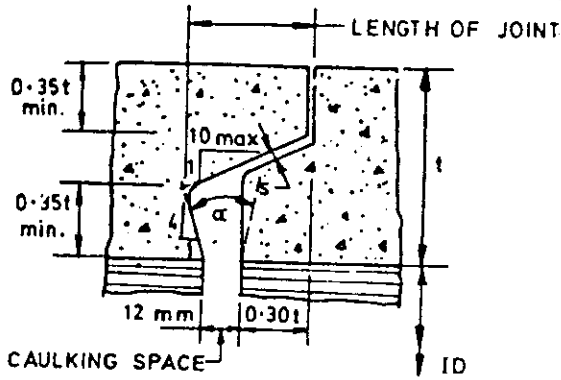

1A Internal Flush Joints

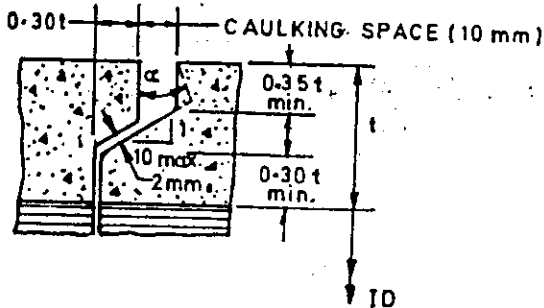

1B External Flush Joints

t = wall thickness
 s = 0.002 of internal diameter or 2 mm, *Min*
 α = included angle not more than 25°
 ID = internal diameter

FIG. 1 DETAILS OF FLUSH JOINTS


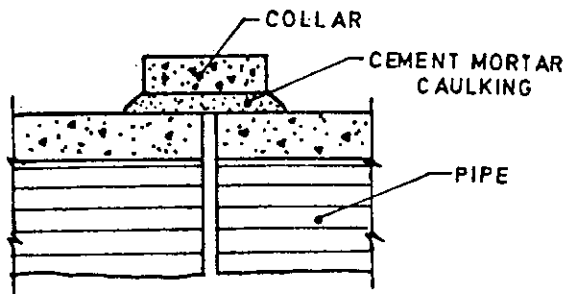



FIG. 2 COLLAR JOINT (RIGID)




NOTE — No. of Z bars : Minimum half the number of longitudinals.

Maximum equal to number of longitudinals.

3A Socket Cage Connected to Barrel Cage by Means of Z Bars




3B Socket Cage Longitudinals Suitably Bent for Connecting to Barrel Cage



3C Cage Made of Continuous Longitudinals

FIG. 3 TYPICAL ARRANGEMENTS OF REINFORCEMENT IN SOCKET FOR SINGLE CAGE

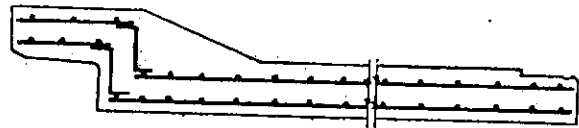

NOTE — No. of Z bars : Minimum half the number of longitudinals.

Maximum equal to number of longitudinals.

4A Socket Cage Connected to Barrel Cage by Means of Z Bars



4B Socket Cage Longitudinals Suitably Bent for Connecting to Barrel Cage



4C Cage Made of Continuous Longitudinals

FIG. 4 TYPICAL ARRANGEMENTS OF REINFORCEMENT IN SOCKET FOR DOUBLE CAGE (USE SUITABLE TYPE OF SPACERS)




TABLE 1 DESIGN AND STRENGTH TEST REQUIREMENTS OF CONCRETE PIPES OF CLASS NP1 — UNREINFORCED NON-PRESSURE PIPES

(Clauses 5.1.1, 5.3 and 7.1)

INTERNAL DIAMETER OF PIPES	BARREL WALL THICKNESS	COLLAR DIMENSIONS		MINIMUM LENGTH OF COLLAR	STRENGTH TEST REQUIREMENT FOR THREE EDGE BEARING TEST, ULTIMATE LOAD
		Minimum Caulking Space	Minimum Thickness		
(1)	(2)	(3)	(4)	(5)	(6)
mm	mm	mm	mm	mm	kN/linear metre
80	25	13	25	150	15.3
100	25	13	25	150	15.3
150	25	13	25	150	15.3
200	25	13	25	150	16.4
225	25	13	25	150	16.4
250	25	13	25	150	16.4
300	30	16	30	150	17.6
350	32	16	32	150	18.4
400	32	16	32	150	18.8
450	35	19	35	200	21.9




TABLE 2 DESIGN AND STRENGTH TEST REQUIREMENTS OF CONCRETE PIPES OF CLASS N₂ — REINFORCED CONCRETE, LIGHT-DUTY, NON-PRESSURE PIPES

(Clauses 5.1.1, 5.1.2, 5.1.3, 5.2.2, 5.3, 6.3.2 and 7.1)

INTERNAL DIAMETER OF PIPES		BARREL WALL THICKNESS	COLLAR DIMENSIONS			REINFORCEMENTS				STRENGTH TEST REQUIREMENTS FOR THREE EDGE BEARING TEST	
Nominal	Actual		Minimum Caulking	Minimum Thickness	Minimum Length	Longitudinal, Mild Steel or Hard-Drawn Steel		Spirals, Hard-Drawn Steel		Load to Produce 0.25 mm Crack	Ultimate Load
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)
mm	mm	mm	mm	mm	mm	Min number	kg/linear metre	kg/linear metre	kg/No.	kN/linear metre	kN/linear metre
80	80	25	13	25	150	6	0.33	0.10	0.13	10.05	15.08
100	100	25	13	25	150	6	0.33	0.12	0.14	10.05	15.08
150	150	25	13	25	150	6	0.33	0.24	0.19	10.79	16.19
200	200	25	13	25	150	6	0.33	0.38	0.22	11.77	17.66
225	225	25	13	25	150	6	0.33	0.46	0.24	12.26	18.39
250	250	25	13	25	150	6	0.33	0.58	0.26	12.55	18.83
300	300	30	16	30	150	8	0.78	0.79	0.71	13.48	20.22
350	350	32	16	32	150	8	0.78	1.13	0.79	14.46	21.69
400	400	32	16	32	150	8	0.78	1.49	0.88	15.45	23.18
450	450	35	19	35	200	8	0.78	1.97	1.48	16.18	24.27
500	500	35	19	35	200	8	0.78	2.46	1.61	17.16	25.74
600	590	45	19	40	200	8	0.78	3.47	1.89	18.88	28.32
700	680	50	19	40	200	8	1.22	4.60	2.27	20.35	30.53
800	790	50	19	45	200	8	1.22	6.71	2.71	21.57	32.36
900	890	55	19	50	200	8	1.22	9.25	3.26	22.80	34.20
1 000	990	60	19	55	200	8	1.76	10.69	3.64	24.27	36.41
1 100	1 090	65	19	60	200	8	1.76	12.74	4.06	25.50	38.25
1 200	1 190	70	19	65	200	8	1.76	15.47	4.52	26.97	40.46
1 400	1 400	75	19	75	200	12	2.64	20.57	5.68	29.42	44.13
1 600	1 600	80	19	80	200	8+8	3.52	25.40	7.20	32.12	48.18
1 800	1 800	90	19	90	200	8+8	3.52	32.74	11.11	35.06	52.59
2 000	2 000	100	19	100	200	12+12	5.28	45.14	14.00	37.76	56.64
2 200	2 200	110	19	110	200	12+12	5.28	56.37	17.00	40.21	60.32

NOTE 1 — If mild steel is used for spiral reinforcement, the weight specified under col 9 and 10 shall be increased to 140/125.

NOTE 2 — Soft grade mild steel wire for spirals may be used for pipes of internal diameters 80 mm, 100 mm and 150 mm only, by increasing weight to 140/84.

NOTE 3 — The longitudinal reinforcement given in this table is valid for pipes up to 2 m effective length for internal diameter of pipe up to 250 mm and up to 3 m effective length for higher diameter pipes.



TABLE 3 DESIGN AND STRENGTH TEST REQUIREMENTS OF CONCRETE PIPES OF CLASS NP3 —
REINFORCED CONCRETE, MEDIUM-DUTY, NON-PRESSURE PIPES

(Clauses 5.1.1, 5.1.2, 5.1.3, 5.2.2, 6.3.2 and 7.1)

NOMINAL INTERNAL DIAMETER OF PIPES	BARREL WALL THICKNESS	REINFORCEMENTS			STRENGTH TEST REQUIREMENTS FOR THREE EDGE BEARING TEST	
		Longitudinal, Mild Steel or Hard-Drawn Steel		Spiral, Hard- Drawn Steel	Load to Produce 0.25 mm Crack	Ultimate Load
		(3)	(4)	(5)	(6)	(7)
(1) mm	(2) mm	Min number	kg/linear metre	kg/linear metre	kN/linear metre	kN/linear metre
80	25	6	0.33	0.15	13.00	19.50
100	25	6	0.33	0.22	13.00	19.50
150	25	6	0.33	0.46	13.70	20.55
200	30	6	0.33	0.81	14.50	21.75
225	30	6	0.33	1.03	14.80	22.20
250	30	6	0.33	1.24	15.00	22.50
300	40	8	0.78	1.80	15.50	23.25
350	75	8	0.78	2.95	16.77	25.16
400	75	8	0.78	3.30	19.16	28.74
450	75	8	0.78	3.79	21.56	32.34
500	75	8	0.78	4.82	23.95	35.93
600	85	6+6	1.18	7.01	28.74	43.11
700	85	6+6	1.18	10.27	33.53	50.30
800	95	6+6	2.66	13.04	38.32	57.48
900	100	6+6	2.66	18.30	43.11	64.67
1 000	115	6+6	2.66	21.52	47.90	71.85
1 100	115	6+6	2.66	27.99	52.69	79.00
1 200	120	8+8	3.55	33.57	57.48	86.22
1 400	135	8+8	3.55	46.21	67.06	100.60
1 600	140	8+8	3.55	65.40	76.64	114.96
1 800	150	12+12	9.36	87.10	86.22	129.33
2 000	170	12+12	9.36	97.90	95.80	143.70
2 200	185	12+12	9.36	113.30	105.38	158.07
2 400	200	12+12	14.88	146.61	114.96	172.44
2 600	215	12+12	14.88	175.76	124.54	186.81

NOTE 1 — The actual internal diameter is to be declared by the manufacturer and the tolerance is to be applied on the declared diameter (see also 0.3.2).


NOTE 2 — Minimum thickness and minimum length of collars shall be the same as that for the next higher size available in NP2 class pipes corresponding to the calculated inner diameter of collars.

NOTE 3 — The longitudinal reinforcement given in this table is valid for pipes up to 2 m effective length for internal diameter of pipe up to 250 mm and up to 3 m effective length for higher diameter pipes.

NOTE 4 — Concrete for pipes above 1 800 mm nominal diameter shall have a minimum compressive strength of 35 N/mm² at 28 days and a minimum cement content of 400 kg/m³.


NOTE 5 — If mild steel is used for spiral reinforcement, the weight specified in col 5 shall be increased to 140/125.

60 45 45 (7)
 60 45 45
 65 55 50
 70 70 55
 75 70 60
 80 65 65
 85 60 60
 90 55 55
 95 50 50
 100 45 45



IS

TABLE 9 SPIGOT AND SOCKET DIMENSIONS OF NP2 AND P1 CLASS PIPES (RUBBER RING ROLL ON JOINT)
 (Clauses 5.3 and 7.2)
 All dimensions in millimetres.

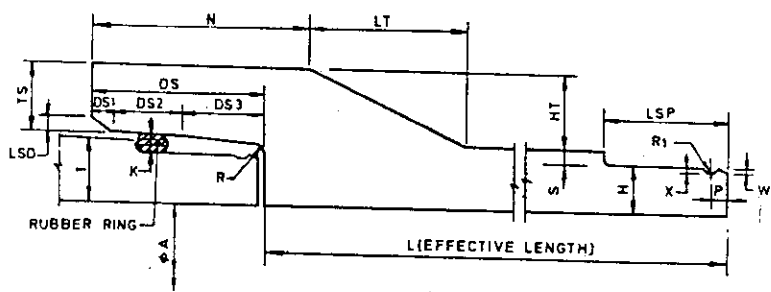

13

PIPE DIAMETER A	RUBBER RING CHORD DIAMETER	RUBBER RING INTERNAL DIAMETER	T	TS	DS	DS1	DS2	DS3	R	LSD	K	N	LT	HT	LSP	P	S	H	X	W	R ₁
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)	(14)	(15)	(16)	(17)	(18)	(19)	(20)	(21)	(22)
80	11	102	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
100	11	120	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
150	11	170	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
200	11	215	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
225	11	225	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
250	11	250	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
300	12	315	30	35	77	9	31	37	3	6	7	107	92	37	55	7.5	6	24	1	1	6
350	12	360	32	37	77	9	31	37	3	6	7	109	96	39	55	7.5	6	26	1	1	6
400	12	400	32	37	77	9	31	37	3	6	7	109	96	39	55	7.5	6	26	1	1	6
450	12	450	35	40	77	9	31	37	3	6	7	109	96	39	55	7.5	6	26	1	1	6
500	12	500	35	40	77	9	31	37	3	6	7	112	104	42	55	7.5	6	29	1	1	6
600	16	590	40	44	102	12	42	48	6	9	9.5	132	106	47	72	10	7.5	32.5	2	2	8
700	16	660	40	44	102	12	42	48	6	9	9.5	132	106	47	72	10	7.5	32.5	2	2	8
800	20	785	45	49	128	15	52	61	6	11	11.5	162	117	52	90	12.5	9.5	35.5	2	2	10
900	20	875	50	56	128	15	52	61	6	11	11.5	162	117	52	90	12.5	9.5	35.5	2	2	10
1 000	22	980	55	60	141	17	57	67	8	12	13.5	169	137	64	99	14	10.5	44.5	2	2	11
1 100	22	1 070	60	65	141	17	57	67	8	12	13.5	171	148	69	99	14	10.5	49.5	2	2	11
1 200	22	1 170	65	71	141	17	57	67	8	12	13.5	173	161	75	99	14	10.5	54.5	2	2	11
1 400	22	1 370	75	82	141	17	57	67	8	15	15	205	195	91	100	15	12	68	2.5	2.5	12
1 600	25	1 560	80	87	165	20	67	78	8	15	15	210	221	103	100	15	12	78	2.5	2.5	12
1 800	25	1 780	90	99	165	20	67	78	8	15	15	215	242	113	100	15	12	88	2.5	2.5	12
2 000	25	1 935	100	109	165	20	67	78	8	15	15	220	264	123	100	15	12	98	2.5	2.5	12
2 200	25	2 130	110	119	165	20	67	78	8	15	15	220	264	123	100	15	12	98	2.5	2.5	12

NOTE 1 — Corners to be rounded off.

NOTE 2 — The dimensions TS, T, H, S, HT and K shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:


Dimensions	Tolerances
T and HT	Same as that of wall thickness given in 7.2.
TS and H	Half the tolerance on wall thickness given in 7.2.
K and S	±0.25 mm for dimensions up to and including 10 mm, and ±0.5 mm for dimensions above 10 mm, 1+1.

TABLE 10 SPIGOT AND SOCKET DIMENSIONS OF NP3 AND NP4 CLASS PIPES (RUBBER RING ROLL ON JOINT)
FROM 80 TO 900 mm DIAMETER

(Clauses 5.3 and 7.2)

All dimensions in millimetres.

IS : 458 - 1988

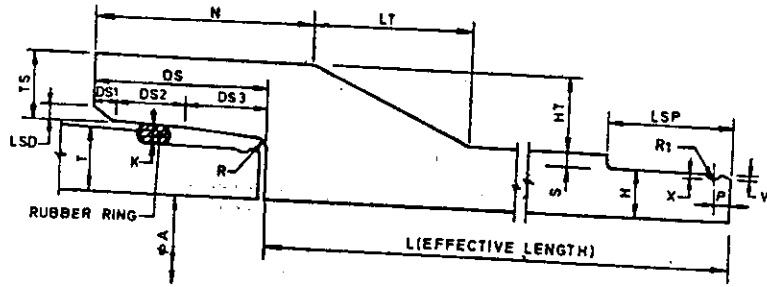

PIPE DIAMETER A	RUBBER RING CHORD DIAMETER	RUBBER RING INTERNAL DIAMETER	T	TS	DS	DS1	DS2	DS3	R	LSD	K	N	LT	HT	LSP	P	S	H	X	W	R ₁
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)	(14)	(15)	(16)	(17)	(18)	(19)	(20)	(21)	(22)
80	11	102	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
100	11	120	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
150	11	170	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
200	11	230	30	38	83	11	38	34	5	6.5	6.5	113	97	39.5	50	7	5.5	24.5	1	1	5.5
225	11	255	30	38	83	11	38	34	5	6.5	6.5	113	97	39.5	50	7	5.5	24.5	1	1	5.5
250	11	275	30	38	83	11	38	34	5	6.5	6.5	113	97	39.5	50	7	5.5	24.5	1	1	5.5
300	12	340	40	51	90	12	42	36	6	7	7	130	130	53	55	7.5	6	34	1	1	6
350	16	435	75	75	120	16	56	48	8	10	10	158	135	78	72	10	8	67	2	2	8
400	16	480	75	75	120	16	56	48	8	10	10	158	135	78	72	10	8	67	2	2	8
450	16	525	75	75	120	16	56	48	8	10	10	158	135	78	72	10	8	67	2	2	8
500	16	570	75	75	150	16	56	48	8	10	10	158	135	78	72	10	8	67	2	2	8
600	20	675	85	85	150	20	70	60	10	12	12	193	153	88.5	90	12	10	75	2	2	10
700	20	765	85	85	150	20	70	60	10	12	12	193	153	88.5	90	12	10	75	2	2	10
800	20	875	95	95	150	20	70	60	10	12	12	197	171	98.5	90	12	10	85	2	2	10
900	20	970	100	100	150	20	70	60	10	12	12	200	180	103.5	90	12	10	90	2	2	10

Note 1 — Corners to be rounded off.

Note 2 — The dimensions *TS*, *T*, *H*, *S*, *HT* and *K* shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

Dimensions

T and *HT*

TS and *H*

K and *S*

Tolerances

Same as that of wall thickness given in 7.2.

Half the tolerance on wall thickness given in 7.2.

±0.25 mm for dimensions up to and including 10 mm, and

± 0.5 mm for dimensions above 10 mm.

TABLE 11 SPIGOT AND SOCKET DIMENSIONS OF NP3 AND NP4 CLASS PIPES FROM 1 000 TO 2 600 mm DIAMETER (RUBBER RING CONFINED JOINT)
(Clauses 5.3 and 7.2)

All dimensions in millimetres.




TABLE II SPIGOT AND SOCKET DIMENSIONS OF NP3 AND NP4 CLASS PIPES FROM 1 000 TO 2 600 mm DIAMETER (RUBBER RING CONFINED JOINT)

(Clauses 5.3 and 7.2)


All dimensions in millimetres.



TABLE II SPIGOT AND SOCKET DIMENSIONS OF NP3 AND NP4 CLASS PIPES FROM 1 000 TO 2 600 mm DIAMETER (RUBBER RING CONFINED JOINT)

(Clauses 5.3 and 7.2)

All dimensions in millimetres.

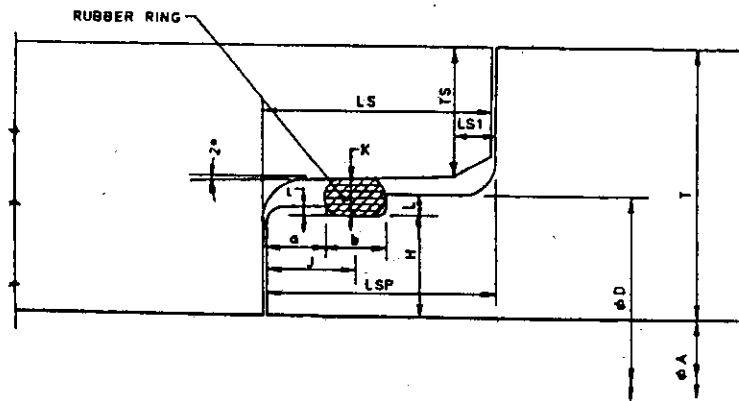

15

PIPE DIAMETER A	RUBBER RING CHORD DIAMETER	RUBBER RING INTERNAL DIAMETER	T	TS	LS	LSI	K	LSP	a	b	J	H	I	L	DIAMETER D
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)	(14)	(15)	(16)
1 000	20	920	115	58	114	20	13	114	25	28	39	42	4	9	1 102
1 100	20	1 003	115	58	114	20	13	114	25	28	39	42	4	9	1 202
1 200	20	1 095	120	60.5	114	20	13	114	25	28	39	44.5	4	9	1 307
1 400	25	1 275	135	67.5	114	20	16	114	25	35	42.5	50	4	10	1 520
1 600	25	1 445	140	72.5	114	25	16	114	25	35	42.5	50	4	10	1 720
1 800	25	1 620	150	77.5	114	25	16	114	25	35	42.5	55	4	10	1 930
2 000	25	1 810	170	87.5	114	25	16	114	25	35	42.5	65	4	10	2 150
2 200	25	1 995	185	95	114	25	16	114	25	35	42.5	72.5	4	10	2 365
2 400	25	2 180	200	102.5	114	25	16	114	25	35	42.5	80	4	10	2 580
2 600	25	2 360	215	110	114	25	16	114	25	35	42.5	87.5	4	10	2 795

NOTE 1 — Corners to be rounded off.


NOTE 2 — The dimensions T, TS, H, L, K and b shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

Dimensions	Tolerances
T	Same as that of wall thickness given in 7.2.
H and TS	Half the tolerances on wall thickness given in 7.2.
K and L	±0.5 mm.
b	±1 mm for 28 mm and ±1.5 mm for 35 mm.

IS 458 - 1984
 DIMENSIONS OF P2 CLASS PIPES (RUBBER RING ON JOINT)
 (see 5.1 and 7.2)



IS : 458 - 1984

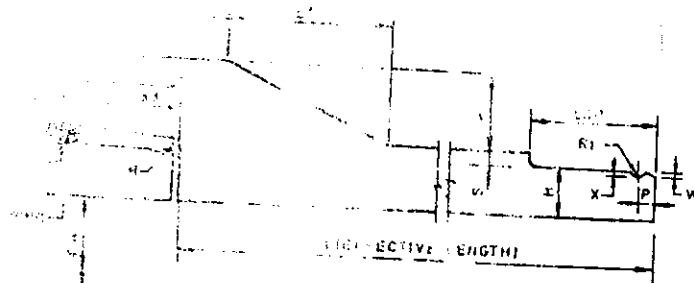

PIPE DIAMETER (mm)	TS	D	T	HT	LSP	P	S	H	X	W	R ₁	
	(11)	(12)	(13)	(14)	(15)	(16)	(17)	(18)	(19)	(20)	(21)	(22)
80	10	80	5	34	50	7	5.5	19.5	1	1	5.5	
100	10	100	5	34	50	7	5.5	19.5	1	1	5.5	
150	10	150	5	34	50	7	5.5	19.5	1	1	5.5	
200	10	200	5	34	50	7	5.5	19.5	1	1	5.5	
250	10	250	5	34	50	7	5.5	19.5	1	1	5.5	
300	10	300	5	34	50	7	5.5	19.5	1	1	5.5	
350	10	350	5	34	50	7	5.5	19.5	1	1	5.5	
400	10	400	5	34	50	7	5.5	19.5	1	1	5.5	
450	10	450	5	34	50	7	5.5	19.5	1	1	5.5	
500	10	500	5	34	50	7	5.5	19.5	1	1	5.5	
600	10	600	5	34	50	7	5.5	19.5	1	1	5.5	
700	10	700	5	34	50	7	5.5	19.5	1	1	5.5	
800	10	800	5	34	50	7	5.5	19.5	1	1	5.5	
900	10	900	5	34	50	7	5.5	19.5	1	1	5.5	
1 000	10	1 000	5	34	50	7	5.5	19.5	1	1	5.5	

Note 1 - Corners to be rounded off.

Note 2 - The dimensions T, S, H, S, HT and K shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:


Dimensions
 T and HT
 TS and H
 K and S

Tolerances
 Same as that of wall thickness given in 7.2.
 Half the tolerance on wall thickness given in 7.2.
 ±0.05 mm for dimensions up to and including 10 mm, and
 ±0.3 mm for dimensions above 10 mm.

TABLE 13 SPIGOT AND SOCKET DIMENSIONS OF P3 CLASS PIPES (RUBBER RING ROLL ON JOINT)

(Classes 5.3 and 7.2)

All dimensions in millimeters.

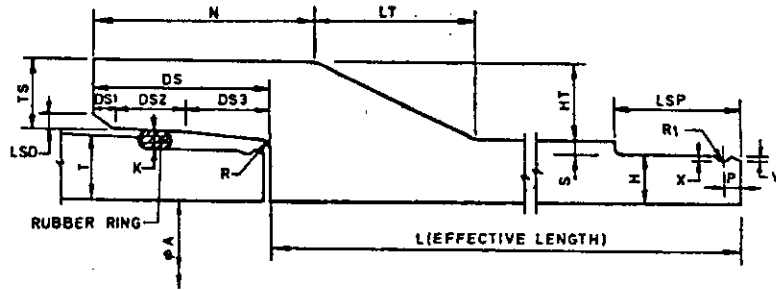

PIPE DIAMETER A	RUBBER RING CHORD DIAMETER	RUBBER RING INTERNAL DIAMETER	T	TS	DS	DS1	DS2	DS3	R	LSD	K	N	LT	HT	LSP	P	S	H	X	W	RI
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)	(14)	(15)	(16)	(17)	(18)	(19)	(20)	(21)	(22)
80	11	102	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
100	11	120	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
150	11	170	25	32.5	70	8	28	34	3	5.5	6.5	95	84	34	50	7	5.5	19.5	1	1	5.5
200	11	230	35	45	83	11	38	34	5	6.5	6.5	120	115	46.5	50	7	5.5	29.5	1	1	5.5
225	11	255	35	45	83	11	38	34	5	6.5	6.5	120	115	46.5	50	7	5.5	29.5	1	1	5.5
250	11	275	35	45	83	11	38	34	5	6.5	6.5	120	115	46.5	50	7	5.5	29.5	1	1	5.5
300	12	340	45	60	90	12	42	36	6	7	7	135	150	62	55	7.5	6	39	1	1	6
350	12	400	55	75	90	12	42	36	6	7	7	145	190	77	55	7.5	6	49	1	1	6
400	12	450	60	80	90	12	42	36	6	7	7	150	200	82	55	7.5	6	54	1	1	6
450	12	525	70	95	90	12	42	36	6	7	7	160	240	97	55	7.5	6	64	1	1	6
500	12	570	75	100	90	12	42	36	6	7	7	165	250	102	55	7.5	6	69	1	1	6
600	16	680	90	120	120	16	56	48	8	10	9.5	190	275	123	72	10	7.5	82.5	2	2	8
700	16	805	105	140	120	16	56	48	8	10	9.5	200	320	143	72	10	7.5	97.5	2	2	8
800	20	915	120	160	150	20	70	60	10	12	12	240	365	164	90	12.5	9.5	110.5	2	2	10

NOTE 1 — Corners to be rounded off.

NOTE 2 — The dimensions TS, T, H, S, HT and K shall conform to the values given in this table as these are critical dimensions. Other dimensions are for guidance only. The following tolerances shall apply on the critical dimensions:

Dimensions

T and HT

TS and H

K and S

Tolerances

Same as that of wall thickness given in 7.2.

Half the tolerance on wall thickness given in 7.2.

±0.15 mm for dimensions up to and including 10 mm, and
±0.3 mm for dimensions above 10 mm.



TABLE 14 WEIGHT OF SPIRALS (HARD-DRAWN STEEL) IN SOCKET OF R/R JOINT RCC PIPES OF DIFFERENT CLASSES (kg/NUMBER)

(Clause 5.3)

INTERNAL DIAMETER OF PIPES (mm)	NP2 CLASS	NP3 CLASS	NP4 CLASS	P1 CLASS	P2 CLASS	P3 CLASS
(1)	(2)	(3)	(4)	(5)	(6)	(7)
80	0.08	0.08	0.08	0.08	0.08	0.08
100	0.09	0.09	0.09	0.09	0.09	0.09
150	0.12	0.12	0.12	0.12	0.12	0.15
200	0.14	0.14	0.21	0.14	0.21	0.35
225	0.15	0.15	0.26	0.15	0.26	0.43
250	0.16	0.16	0.31	0.16	0.31	0.51
300	0.45	0.45	0.53	0.45	0.53	0.84
350	0.51	0.64	0.64	0.51	0.74	1.24
400	0.56	0.71	0.71	0.56	0.99	1.66
450	0.63	0.76	0.76	0.63	1.23	2.26
500	0.68	0.87	1.08	0.68	1.57	2.85
600	0.81	1.00	2.12	1.52	2.88	4.74
700	0.92	2.16	3.02	1.79	3.96	6.79
800	1.14	2.87	4.67	2.04	6.28	9.99
900	1.50	4.06	6.03	2.63	8.29	—
1 000	1.91	—	—	3.33	1.29	—
1 100	2.34	—	—	4.08	—	—
1 200	2.80	—	—	4.90	—	—
1 400	3.82	—	—	—	—	—
1 600	5.64	—	—	—	—	—
1 800	7.25	—	—	—	—	—
2 000	11.78	—	—	—	—	—
2 200	12.88	—	—	—	—	—

NOTE 1 — Longitudinal reinforcement shall be proportional to the length of socket cage as given in Tables 2 to 7.

NOTE 2 — If mild steel is used for spiral reinforcement, the weight specified above shall be increased to 140/125.

5.4 Cover — The minimum clear cover for reinforcement in pipes and collars shall be as given below:

	<i>Minimum Clear Cover mm</i>
a) Barrel thickness	
1) Up to and including 25 mm	6
2) Over 25 mm and up to and including 30 mm	8
3) Over 30 mm and up to and including 75 mm	10
4) Over 75 mm	15
b) At spigot steps	4
c) At end of longitudinals	5


NOTE — An effective means shall be provided for maintaining the reinforcement in position and for ensuring correct cover during manufacture of the unit. Spacers for this purpose shall be of rustproof material or of steel protected against corrosion.

6. MANUFACTURE

6.1 General — The methods of manufacture shall be such that the form and dimensions of the finished pipe are accurate within the limits specified in this standard. The surfaces and edges of the pipes shall be well defined and true, and their ends shall be square with the longitudinal axis.

6.2 Concrete Mixing — Concrete shall be mixed in a mechanical mixer.

6.2.1 Mixing shall be continued until there is a uniform distribution of the materials and the mass is uniform in colour and consistency, but in no case shall the mixing be done for less than two minutes.



6.2.2 Water-cement ratio shall be less than 0.5.

6.2.3 The concrete shall be placed before setting has commenced. It should be ensured that the concrete is not dropped freely so as to cause segregation. The concrete shall be consolidated by spinning, vibrating, spinning combined with vibrations, or other appropriate mechanical means.

6.3 Reinforcement Cages — Reinforcement cages for pipes shall extend throughout the pipe barrel. The cages shall consist of spirals or rings and straights of hard-drawn steel wire or mild steel rod and may be circular. Circular cages and longitudinal reinforcement shall be placed symmetrically with respect to the thickness of the pipe wall. The spirals shall end in a complete ring at both the ends of a pipe.

6.3.1 Pipes having barrel thickness above 75 mm shall have double reinforcement cage and the amount of steel in the outer cage shall be 75 percent of the mass of the inner cage whilst the total shall conform to the requirements specified in the relevant tables of this standard. The total longitudinal steel per pipe shall be as given in the relevant tables of the standard but the distribution shall be such that the round shape of the cage is not disturbed.

6.3.2 Diagonal reinforcement may be provided in pipes for which the cages are not welded so as to help in binding the cage securely. It shall, however, be ensured that the clear cover for any reinforcement is not below the limits specified in 5.4. If diagonal reinforcement is provided, it shall be considered as part of the longitudinal reinforcement given in Tables 2 to 7.

6.3.3 Single reinforcement cage shall be located near the inner surface of the pipe with adequate clear cover.

6.4 Curing

6.4.1 Water Curing — Pipes manufactured in compliance with this standard shall be water cured for a period of not less than 2 weeks in case of pipes made from ordinary Portland cement or Portland slag cement or Portland pozzolana cement or hydrophobic Portland cement, and not less than 1 week in case of pipes made from rapid-hardening Portland cement or 43 grade ordinary Portland cement. Pipes may be water cured by immersing in water, covering with water-saturated material or by a system of perforated pipes, mechanical sprinklers, porous hose, or by any other approved method that will keep the pipe moist during the specified curing period. In the case of large pipe projecting partly above the water level, the projected portion shall be kept wet by any suitable means.

6.4.2 Steam Curing — Steam curing of concrete pipes may be permitted provided the requirements of pressure and non-pressure steam curing are fulfilled

and the pipes conform to the requirements of this specification.

6.4.3 The manufacturer may, at his option, combine the methods described in 6.4.1 and 6.4.2 as long as the specified strength is attained.

7. DIMENSIONS

7.1 Pipes — The internal diameter, wall thickness, length and thickness of collar of pipes, the minimum reinforcements and strength test requirements for different classes of pipes (see 3.1), shall be as specified in Tables 1 to 7. The manufacturer shall inform the purchaser of the effective length of spigot and socket, and flush jointed pipes that he is able to supply. For collar jointed pipes, effective length shall be 2 m up to 250 mm nominal diameter pipes and 2.5, 3.0, 3.5 or 4.0 m for pipes above 250 mm nominal diameter.

NOTE — Pipes of internal diameter, wall thickness and length of barrel and collar other than those specified in 7.1 may be supplied by mutual agreement between the purchaser and the supplier. In such case, the design of pipes submitted to the purchaser shall include all standard details as covered in Tables 1 to 7.

7.2 Tolerances — The following tolerances shall be permitted:

Dimensions	Tolerances
a) Overall length	±1 percent of standard length
b) Internal diameter of pipes or socket:	
1) Up to and including 300 mm	±3 mm
2) Over 300 mm and up to and including 600 mm	±5 mm
3) Over 600 mm and up to and including 1 200 mm	±7 mm
4) Over 1 200 mm	±10 mm
c) Wall thickness:	
1) Up to and including 30 mm	±2 mm
2) Over 30 mm and up to and including 50 mm	±3 mm
3) Over 50 mm and up to and including 65 mm	±4 mm
4) Over 65 mm and up to and including 80 mm	±5 mm
5) Over 80 mm and up to and including 95 mm	±6 mm
6) Over 95 mm	±7 mm



requirements of this
 , at his option, com-
 4.1 and 6.4.2 as long
 ed.

eter, wall thickness,
 pipes, the minimum
 requirements for
 3.1), shall be as
 manufacturer shall
 tive length of spigot
 s that he is able to
 effective length shall
 diameter pipes and
 es above 250 mm

er, wall thickness and
 than those specified
 agreement between
 such case, the design
 use all include all
 es 1. 7.

olerances shall be

Tolerances

±1 percent of
 standard length

±3 mm

±5 mm

±7 mm

±10 mm

±2 mm

±3 mm

±4 mm

±5 mm

±6 mm

±7 mm

NOTE — In case of pipes with flexible rubber ring joints, the tolerance on thickness near the ends will have to be reduced. Near the rubber ring joints, the tolerance on thickness shall be as given in Tables 9 to 13.

8. WORKMANSHIP AND FINISH

8.1 Finish — Pipes shall be straight and free from cracks except that craze cracks may be permitted. The ends of the pipes shall be square with their longitudinal axis so that when placed in a straight line in the trench, no opening between ends in contact shall exceed 3 mm in pipes up to 600 mm diameter (inclusive), and 6 mm in pipes larger than 600 mm diameter.

8.1.1 The outside and inside surfaces of the pipes shall be smooth, dense and hard, and shall not be coated with cement wash or other preparation unless otherwise agreed to between the purchaser and the manufacturer or the supplier. For better bond, inner surface of the collar may be finished rough.

8.1.2 The pipes shall be free from defects resulting from imperfect grading of the aggregate, mixing or moulding.

8.1.3 Pipes shall be free from local dents or bulges greater than 3.0 mm in depth and extending over a length in any direction greater than twice the thickness of barrel.

8.1.4 Pipes may be repaired, if necessary, because of accidental injury during manufacture or handling and shall be accepted if in the opinion of the purchaser, the repairs are sound and appropriately finished and cured, and the repaired pipe conforms to the requirements of this specification.

8.2 Deviation from Straight — The deviation from straight in any pipe throughout its effective length, tested by means of a rigid straight edge parallel to the longitudinal axis of the pipe shall not exceed, for all diameters, 3 mm for every metre run.

9. TESTS

9.1 Test Specimens — All pipes for testing purposes shall be selected at random from the stock of the manufacturer and shall be such as would not otherwise be rejected under this standard.

9.1.1 During manufacture, tests on concrete shall be carried out as detailed in IS : 456-1978¹. The manufacturer shall supply, when required to do so by the purchaser or his representative, the results of compressive tests of concrete cubes (see 4.5.1) and split tensile tests of concrete cylinders (see 4.5.2) made from the concrete used for the pipes. The manufacturer shall supply cylinders or cubes for test purposes required by the purchaser, and such cylinders or cubes shall withstand the tests prescribed in 4.5.1 and 4.5.2. Every pressure pipe shall be tested by the manufacturer for the hydrostatic test

¹Code of practice for plain and reinforced concrete (third revision).

pressure (see 3.1). For non-pressure pipes, percent of the pipes shall be tested for hydrostatic test pressure.

9.2 The specimens of pipes selected in accordance with 9.1 and subjected to the following tests in the given sequence shall withstand the design loads:

- a) Hydrostatic test, as described in IS : 3597-1985¹;
- b) Three-edge bearing test as described in IS : 3597-1985¹; and
- c) Absorption test, as described in IS : 3597-1985¹.

9.2.1 The manufacturer shall regularly carry out absorption tests on specimens corresponding to the pipe manufactured and shall provide sufficient proof to the purchaser that the pipes supplied satisfy the absorption test. If, however, the purchaser desires to have absorption test carried out on any sample the same may be done on mutually agreed terms.

9.2.2 The absorption test when conducted in accordance with the method described in 6 of IS : 3597-1985¹, shall satisfy the following requirements:

- a) Absorption in the first 10 minutes shall not exceed 2.5 percent of the dry mass, and
- b) Total absorption at the end of 24 hours shall not exceed 6.5 percent of the dry mass.

10. SAMPLING AND INSPECTION

10.1 Scale of Sampling

10.1.1 Lot — In any consignment, all the pipes of same class, same size and belonging to the same mix of concrete shall be grouped together to constitute a lot.


10.1.2 For ascertaining the conformity of the material to the requirements of this specification, samples shall be tested from each lot separately.

10.1.3 The number of pipes to be selected from the lot shall depend on the size of the lot and shall be according to Table 15.

TABLE 15 SCALE OF SAMPLING AND PERMISSIBLE NUMBER OF DEFECTIVES

No. of PIPES IN THE LOT	FOR REQUIREMENTS UNDER 7 AND 8		SAMPLE SIZE FOR TESTS UNDER 9.2 (EXCLUDING ULTIMATE LOAD TEST)
	Sample Size	Permissible Number of Defectives	
(1)	(2)	(3)	(4)
Up to 50	8	0	2
51 to 100	13	1	3
101 to 300	20	2	5
301 to 500	32	3	7
501 and above	50	5	10

¹Methods of tests for concrete pipes (first revision).



IS : 458 - 1988

10.1.3.1 These pipes shall be selected at random. In order to ensure the randomness of selection, procedures given in IS : 4905-1968¹ may be followed.

10.2 Number of Tests and Criteria for Conformity

10.2.1 All the pipes selected according to 10.1.3 shall be inspected for dimensional requirements (see 7), finish (see 8.1) and deviation from straight (see 8.2). A pipe failing to satisfy one or more of these requirements shall be considered as defective.

10.2.1.1 The lot shall be declared as conforming to these requirements if the number of defectives found in the sample does not exceed the number of defectives given in col 3 of Table 15.

10.2.2 The lot having found satisfactory shall be further subjected to the tests given under 9.2 except ultimate load test. For this purpose, the number of pipes given in col 4 of Table 15 shall be selected from the lot. These pipes shall be selected from those that have satisfied the requirements given in 10.2.1. For ultimate load test, the number of pipes to be checked shall be according to mutual agreement between the purchaser and the manufacturer. However, ultimate load test shall not be done for a lot size of 20 pipes or less.

¹Methods of random sampling.

10.2.2.1 The lot shall be declared as conforming to the requirements of this specification if there is no failure under 10.2.2.

11. MARKING


11.1 The following information shall be marked on each pipe:

- a) Name of manufacturer or his registered mark or both,
- b) Class and size of pipe, and
- c) Date of manufacture.

The above information shall be clearly marked on outside only for pipes up to and including 350 mm internal diameter, and both outside and inside for pipes above 350 mm internal diameter.

11.1.1 Each pipe may also be marked with the Standard Mark.

NOTE — The use of the Standard Mark is governed by the provisions of the Bureau of Indian Standards Act, 1986 and the Rules and Regulations made thereunder. The Standard Mark on products covered by an Indian Standard conveys the assurance that the products have been produced to comply with the requirements of that standard under a well defined system of production, testing and quality control which is devised and supervised by BIS and operated by the producer. Standard marked products are also continuously checked by BIS for conformity to that standard as a further safeguard. Details of conditions under which a licence for the use of the Standard Mark may be granted to manufacturers or producers may be obtained from the Bureau of Indian Standards.



Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 1986* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designation. Enquiries relating to copyright be addressed to the Director (Publication), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the latest issue of 'BIS Handbook' and 'Standards Monthly Additions'.

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002
Telephones: 323 01 31, 323 33 75, 323 94 02

Telegrams: Manaksanstha
(Common to all offices)

Regional Offices:

	Telephone
Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg NEW DELHI 110002	323 76 17, 323 38 41
Eastern : 1/14 C.I.T. Scheme VII M, V.I.P. Road, Maniktola CALCUTTA 700054	{ 337 84 99, 337 85 00 337 86 26, 337 91 21
Northern : SCO 335-336, Sector 34-A, CHANDIGARH 160022	{ 60 38 41 60 20 21
Southern : C.I.T. Campus, IV Cross Road, CHENNAI 600113	{ 235 02 16, 235 04 41 235 15 19, 235 23 11
Western : Manakalaya, E9 MIDC, Marol, Andheri (East) MUMBAI 400093	{ 832 92 95, 832 78 51 832 78 91, 832 78 91
Branches : AHMADABAD. BANGALORE. BHOPAL. BHUBANESHWAR. COIMBATORE. FARIDABAD. GHAZIABAD. GUWAHATI. HYDERABAD. JAIPUR. KANPUR. LUCKNOW. NAGPUR. PATNA. PUNE. THIRUVANANTHAPURAM.	